



## Life Cycle Assessment and Characterization of Tincal Ore Reinforced Polyester and Vinylester Composites

Emrah Yilmaz<sup>1\*</sup> , Ercan Aydoğmuş<sup>2</sup> , Ahmet Demir<sup>3</sup> 

<sup>1</sup>Düzce University, Faculty of Engineering, Department of Civil Engineering, Düzce, Türkiye

<sup>2</sup>Firat University, Faculty of Engineering, Department of Chemical Engineering, Elazığ, Türkiye

<sup>3</sup>Düzce University, Faculty of Arts and Sciences, Department of Physics, Düzce, Türkiye

**Abstract:** In this study, the quality performance, compressive strength, surface hardness, electrical conductivity, and life cycle assessment (LCA) of the composites produced by reinforcing tincal ( $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$ ) into polyester and vinylester resins at different rates have been determined. Tincal ore, which is ground with a particle size of 74-149 microns, is dried in an oven at 105 °C for 2 hours and then added to the resins at the ratios of 0 wt.%, 1 wt.%, 2 wt.%, and 3 wt.%. According to the results obtained, it has been determined that the compressive strength and Shore D hardness of the composite raises as the tincal mass ratio increases up to certain amounts. According to the mechanical test results, it is found that 3 wt.% tincal reinforcement maximized the compressive strength of the polyester composite, and 2 wt.% tincal reinforcement maximized the compressive strength of the vinylester composite. In the electrical conductivity test results, it is seen that the first relaxation time of the polyester composite is  $2.14 \cdot 10^{-4}$  s and the relaxation times of vinylester composite vary between  $10^{-4}$  and  $10^{-6}$  seconds. LCA results showed that vinylester composite had more environmental effects than polyester composite except for ozone layer depletion (ODP) effect. Although there is a partial increase (<0.5%) in the environmental impact of composites with tincal reinforcement, it is thought that the increase in the technical performance of the composites will tolerate this partial increase.

**Keywords:** Polyester, vinylester, tincal, hardness, compressive strength, dielectric properties, life cycle assessment.

**Submitted:** July 20, 2022. **Accepted:** November 07, 2022.

**Cite this:** Yilmaz E, Aydoğmuş E, Demir A. Life Cycle Assessment and Characterization of Tincal Ore Reinforced Polyester and Vinylester Composites. JOTCSB. 2022;5(2):183-94.

**\*Corresponding author. E-mail:** [emrahyilmaz@duzce.edu.tr](mailto:emrahyilmaz@duzce.edu.tr) .

### INTRODUCTION

Resins are widely used in many different sectors as the basic raw material in the production of high-performance composite materials. Some of the resins commonly used in the production of fiber-reinforced composite materials are polyester, vinylester, polyurethane, and epoxy resins (1-8). Many natural and synthetic fillers are preferred to increase the technical properties of materials obtained from resins and to reduce the amount of petrochemicals used. With the help of these additives and fillers, some physical and chemical

properties of the synthesized products can be improved (9-15). Besides, there are improvements in the mechanical and thermal properties of composite materials produced from resins reinforced with various additives and fillers (16).

In a study in the literature, it has been determined that the fire safety performance of the composites obtained by adding boron nitride to the epoxy resin increases. It has been observed that the composite materials produced by reinforcing different proportions of boron nitride (filler) into vinylester

resin have improvements in impact, hardness, and abrasion resistance (17,18).

In another study, composite samples are obtained by reinforcing unsaturated polyester with borax at different mass ratios. It has been observed that the addition of certain amounts of borax increases the mechanical strength, Shore D hardness, and thermal conductivity coefficient of polyester composites (19). There is also a need to make environmental assessments in studies to increase the performance of such resin composites. For example, the life cycle assessment (LCA) method is used in environmental sustainability studies of composite materials (20-22). In the literature, there are studies for the production of composite materials and determining the environmental performance of these materials by LCA method (23-25). With LCA studies, environmental effects of composite materials such as climate change impact, acidification, and eutrophication potentials are shared transparently (26,27).

In this research, composite materials have been produced by reinforcing tincal at different rates into orthophthalic-based unsaturated polyester and bisphenol-A epoxy-based vinylester resins. It was determined that certain amounts of tincal reinforcement increase the compressive strength and surface hardness of polyester and vinylester composites. In addition, the dielectric properties of the produced composites and by LCA method their environmental effects were investigated.

## MATERIALS AND METHODS

Unsaturated polyester (UP), methyl ethyl ketone peroxide (MEKP), and cobalt octoate (Co Oc) components were supplied from Turkuaz Polyester. Vinylester resin and its components were purchased from Poliya Company (Turkey). Besides, tincal used in this study was supplied from the Eti Maden (Eskişehir Kirka Boron) factory.

Tincal was added to the UP at different rates (0 wt.%, 1 wt.%, 2 wt.%, and 3 wt.%) and mixed at 1000 rpm for 4 minutes. After adding 0.5 wt.% Co Oc and 1.5 wt.% MEKP, respectively, at room temperature at a mixing speed of 750 rpm for 90 seconds, they were poured into standard molds. After waiting 24 hours for the curing of the obtained samples, necessary tests and analyses were carried out (28-35).

Also, tincal was added to the bisphenol-A epoxy-based vinylester resin. After providing a homogeneous mixture of vinylester resin and tincal, certain amounts of the hardener were added and the mixture was mixed and heated (600 rpm, 2 min, and 45 °C). After the mixture obtained was poured into standard molds and waited for one day for curing, necessary tests and analyses were carried out.

Ultrasonic water bath was used to prevent air bubbles that may occur in the prepared mixtures. Besides, mold release agents are applied to standard steel cylindrical molds, allowing the samples to come out easily. In Figure 1, the mixtures prepared under laboratory conditions and the samples obtained are shown.



**Figure 1:** Preparation of tincal-reinforced vinylester and polyester composites.

As seen in Figure 2, the samples are produced in a cylindrical shape with a diameter/length ratio of  $\frac{1}{2}$  (40 mm/80 mm). Compressive strength is performed by ASTM C 579-01. In the experimental


study, a loading rate of 41MPa/min is applied for all samples. Three samples are produced from each mixture to perform the compressive strength.



**Figure 2:** Tincal-reinforced composite samples before and after compressive strength test.

Shore D hardness tests were carried out by ISO 868 (ASTM D 2240) standard. As seen in Figure 3, cylindrical samples with a diameter of 4 cm are used to determine the hardness values of polyester


and vinylester composites. Hardness measurements have been made from 5 different points on 3 different samples and calculated by averaging.

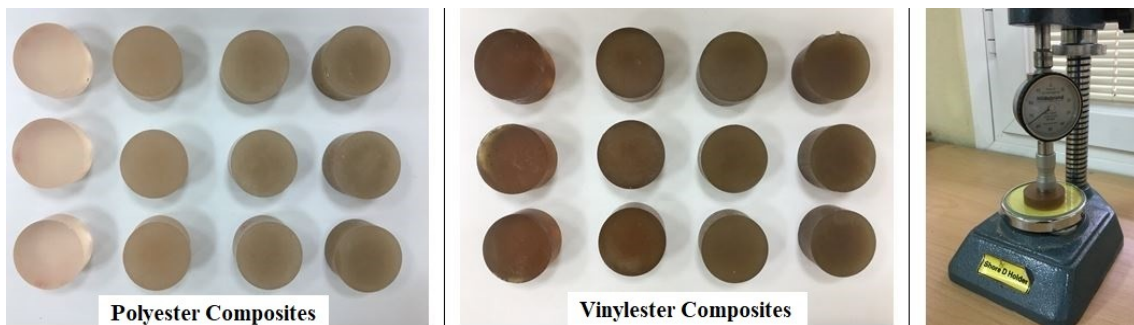

**Figure 3:** Shore D hardness testing of polyester and vinylester composites.

Samples with a diameter of 4 cm were used to determine the dielectric properties of the composites (Figure 4). The dielectric properties

have been measured with the Novacontrol Alpha-A impedance analyzer at a temperature of 300 K in the frequency range of 10 Hz and 10 MHz.

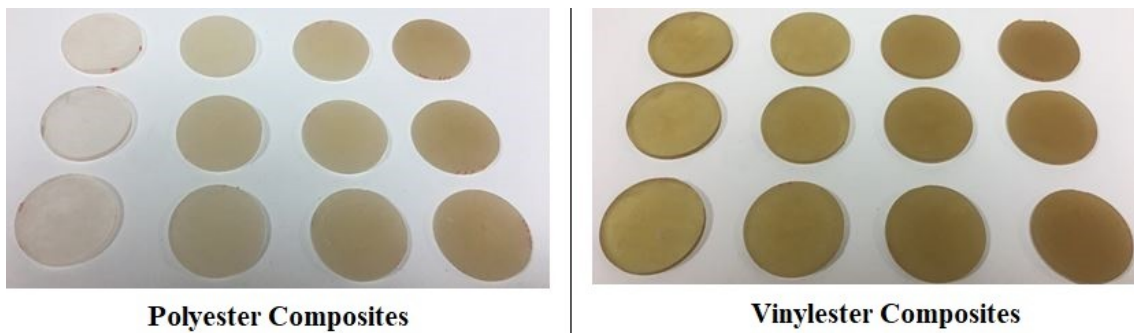

**Figure 4:** Cylindrical samples cut for determination of dielectric properties of composites.


**Life Cycle Assessment**

In this study, ISO 14040 and ISO 14044 standards were used to evaluate the environmental impact of the composite materials produced (36).

**Purpose and Scope**

The aim of the study is to estimate the main environmental effects of polyester and vinylester composites produced with tincal reinforcement at different rates. The system boundaries of the

presented composites follow a cradle-to-gate approach and include manufacturing steps of polyester and vinylester composites. The functional basis chosen for this study is the production of 1 kg of tincal reinforced resin composites. In the life cycle analysis shown in Figure 5, raw material procurement (1), transportation of raw materials to the mixing laboratory (2), and composite products in the laboratory (3) stages.

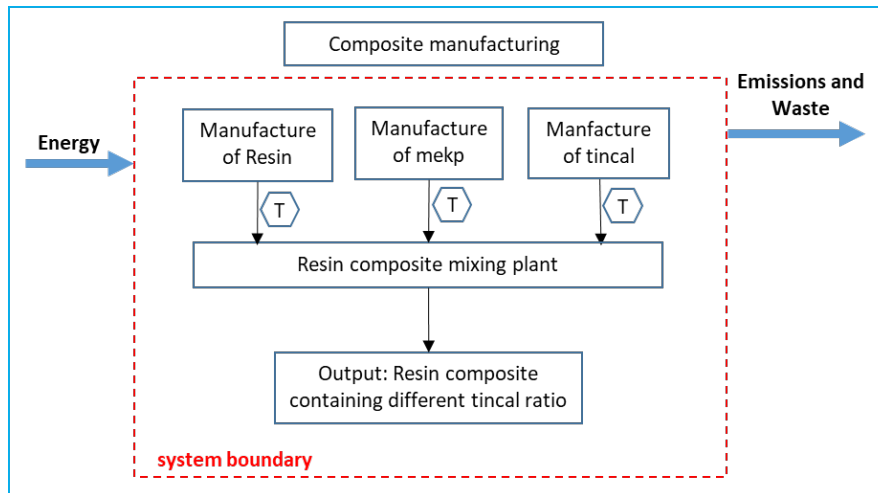

**Figure 5:** The system boundary of tincal reinforced resin composite production (T: transport).

**Inventory Analysis**

The production process of the examined composites is explained in detail in the sections above. The inventory data presented in Table 1 were obtained from laboratory measurements as part of the experimental work conducted in this study and converted to the functional unit “1 kg of tincal-reinforced resin composite”. It is assumed

that all transportation is done by road using diesel fuel. A distance of 100 km is assumed to transport all raw materials to the mixing plant. The mixers and ultrasonic baths used in the preparation process of resin composites are low voltage and 0.022 kWh energy is used to produce 1 kg of resin composite. Life cycle inventory data is taken from the Ecoinvent V3.5 database.

**Table 1:** Inventory for the production of 1 kg of tincal-reinforced resin composites.


Materials	Resins (g) (polyester and vinylester)	Co Oc (g)	MEKP (g)
0 wt. %	980	4.90	14.70
1 wt. %	971	4.86	14.57
3 wt. %	952	4.76	14.28

**Impact Assessment**

LCA modeling was performed in SimaPro 9.1.1.1. As in similar studies (37), CML-IA baseline method created by Center for Environmental Sciences (Leiden University) has been chosen for life cycle impact assessment. Six environmental impact categories are considered in the analysis, including climate change, acidification, eutrophication, fossil fuel, photochemical oxidation, and ozone depletion.

**RESULTS AND DISCUSSIONS**


In Figure 6, the compressive strength values of tincal reinforced polyester and vinylester composite samples are seen comparatively. When the graph is examined, it is seen that the highest compressive strength value (124.95 MPa) is reached when 2 wt.% tincal is added to the vinylester resin. When 2 wt.% tincal is added to the vinylester resin, the compressive strength increases by 4.2%. It has been determined that the compressive strength increases with the increase in the amount of tincal in the polyester resin. When 3 wt.% tincal is added to the polyester resin, the compressive strength raises by 14.6%.

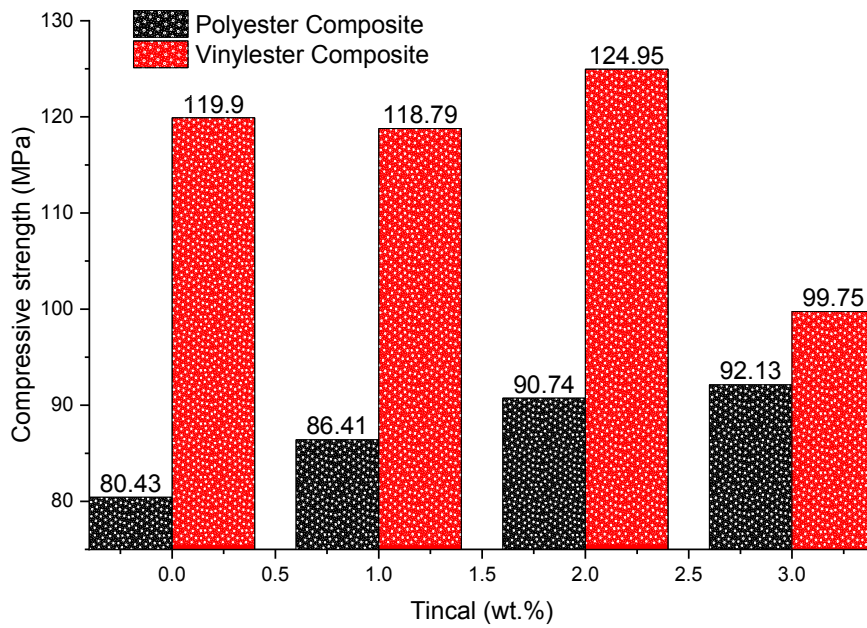

**Figure 6:** Compressive strength values of tincal reinforced resin composites.

In Figure 7, Shore D hardness of tincal reinforced resin composites is compared. The addition of tincal up to 2 wt.% to the vinylester resin increased the surface hardness (3.6%) of the composite. However, the addition of tincal up to 3 wt.% decreases both Shore D hardness of the

vinylester composite. The addition of tincal up to 2 wt.% to the orthophthalic-based polyester resin increases the surface hardness (4.1%) of the composite. However, up to 3%, tincal reinforcement slightly decreases Shore D hardness of the polyester composite.

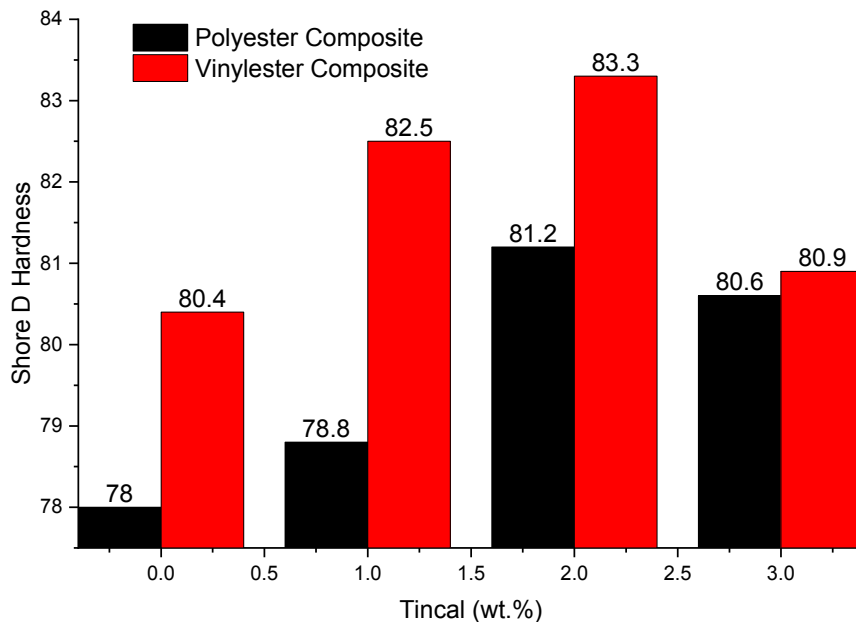

**Figure 7:** Shore D hardness values of tincal reinforced resin composites.

The images of tincal reinforced resin composites after compression tests are given in Figure 8. The vinylester composite samples do not disperse after the compression test and the experiments are

completed with a shortening in height. It is in the form of deformation that occurs with an overlapping agglomeration in the middle regions of the samples. However, the lengths of the polyester


composites are shortened and the samples are deformed vertically. It has been observed that the shortening in length decreases as the amount of

tincal increases. In contrast to the vinylester samples, cracking occur in the polyester composites.



**Tincal Reinforced Polyester Composites**

**Tincal Reinforced Vinylester Composites**

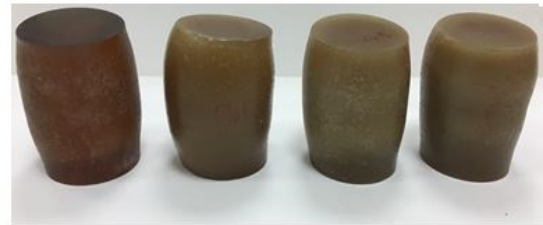

**Figure 8:** Tincal-reinforced composite specimens after compression strength test.

### Dielectric Polarization and Relaxation Mechanisms of Tincal-Reinforced Resin Composites


It provides information about the dielectric properties of materials, and their mechanisms such as conduction, and polarization/relaxation. Many parameters such as thickness, structure, and surface area of the material are effective when examining dielectric properties. With the help of these parameters, real and imaginary dielectric constants are obtained from the capacitance and conductance value of the material. While the real dielectric constant ( $\epsilon'$ ) is a measure of the resistance of the material against charge transmission in its internal structure, the imaginary dielectric constant ( $\epsilon''$ ) is a measure of the energy lost during the charge transition in response to the

material to the electric field. Since these two parameters do not react to the electric field at the same time, a phase difference occurs between them. However, to obtain comprehensive information about the conduction and polarization/relaxation mechanisms in the material, it is necessary to look at the loss tangent, which is defined as the ratio of energy loss to resistance and is a measure of the phase difference angle.

$$\epsilon^* = \epsilon' - j \times \epsilon'' \quad (\text{Eq. 1})$$

$$\tan(\delta) = \frac{\epsilon''}{\epsilon'} \quad (\text{Eq. 2})$$

In Figure 9, the dielectric properties of the tincal-reinforced polyester composite are shown.

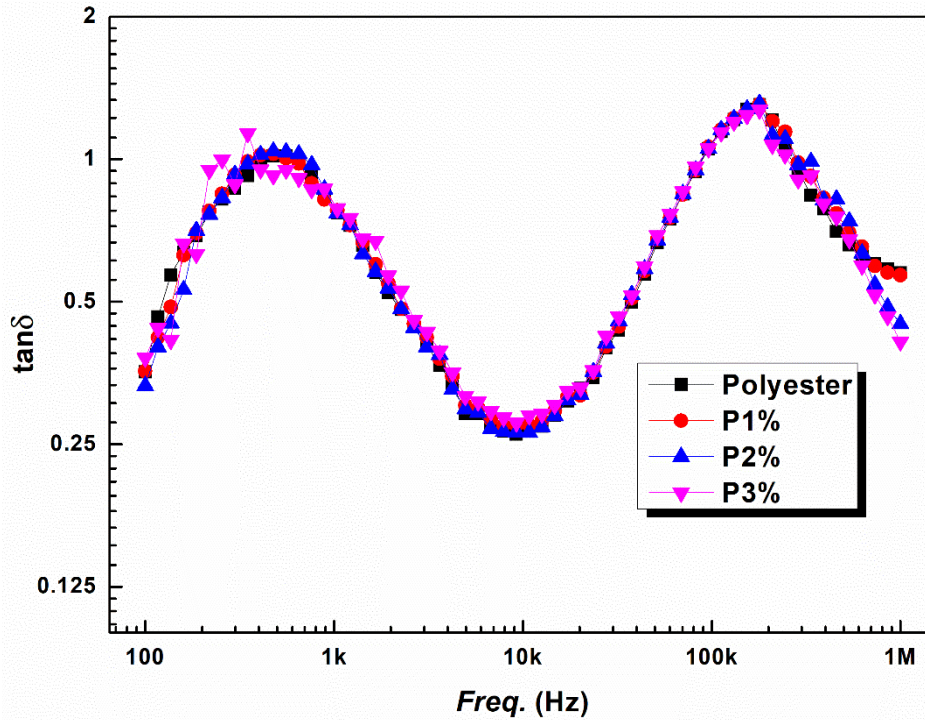


**Figure 9:** Dielectric properties of tincal-reinforced polyester composites.

When Figure 8 is examined, it is seen that there is no change in the  $\tan(\delta)$  or dielectric properties of the materials with doping, but two spot frequencies (475 Hz and 175 kHz) with full polarization is provided for each material. Alternating current at frequencies ranging from 100 Hz to 1 MHz is applied to these materials and they are exposed to an electric field. From 100 Hz, positive charges and negative charges start to polarize in the direction of the field by forming dipoles, and after this frequency, all polarized dipoles start the relaxation process. The relaxation process can be roughly described by the following spot frequency-period relationship.

$$\omega \times \tau = 1 \quad (\text{Eq. 3})$$


According to this relationship, the first relaxation time for all the materials is obtained as  $2.14 \cdot 10^{-4}$  s. The polarization type that completes the relaxation in this time interval is dipole or Maxwell-Wagner polarization. In other words, dipole or Maxwell-Wagner type polarization takes place around 475 Hz in all materials. This relaxation process continues up to about 10 kHz according to Figure 8. After 10 kHz, all of the dipoles begin to polarize again in the direction of the applied AC (alternating current) field, and full polarization is achieved a second time around 175 kHz. According to Equation 3, the relaxation process here is obtained as  $9 \cdot 10^{-7}$  s. The relaxation time at this spot frequency indicates that the polarization mechanism shifts from dipole or Maxwell-Wagner type polarization to ionic polarization.

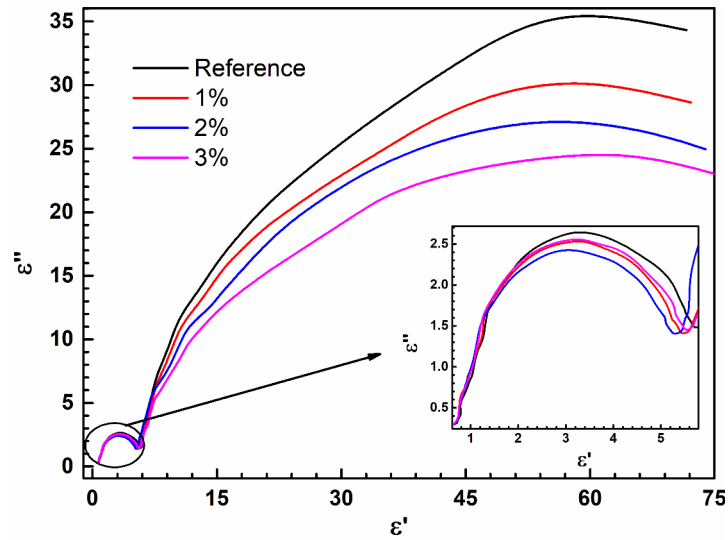

**Figure 10:** Cole-Cole diagram of tincal reinforced vinylester composites.

It contains at least one semicircle for materials that operate as a mechanism of characteristics, polarization, and relaxation of dielectric properties as a smooth behavior and is known as Cole-Cole Diagram. The completion of a semicircle can be depicted with an RC circuit in the material. If an unfinished semicircle reveals that the polarization is realized, but the relaxation does not occur, such behavior means that there is no resistance to polarization. Thus, the depicted circuit can be expressed as a single capacitor in this case. In Figure 10, it is seen that a semicircle is completed in all of the vinylester composites with tincal reinforced vinylester and the continuation of a quarter circle. In this form, the materials can be expressed by a capacitor depiction in the series with an RC circuit consisting of an electrically

connected resistance (R) and a capacitor (C) in parallel with each other in the internal structure. This depicted circuit is called an equivalent circuit and its diagram is as in Figure 11. Equality is used on the top of the semicircle to calculate relaxation times from Cole-Cole diagrams. According to Figure 10 is examined, the relaxation times of vinylester and tincal reinforced vinylester composites vary between  $10^{-4}$  and  $10^{-6}$  seconds. Also, it is seen that their amplitude increases with reinforcement rates in the first and second semicircles. We can say that the increase in amplitude reduces relaxation times. Finally, polarization and relaxation mechanisms of tincal reinforced vinylester composite composites can be attributed to the dipole type relaxation, which we call Maxwell Wagner or orientation.

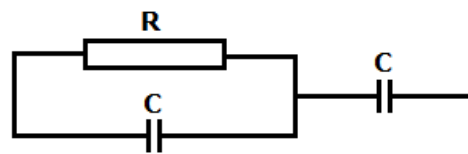

**Figure 11:** Tincal reinforced resin composites equivalent circuit diagram.

**Environmental Sustainability Assessment**

The environmental impact results for the production of 1 kg of tincal reinforced polyester and vinylester resin composites are presented in table 2. The total CC effect of polyester composite (P (3 wt.%) and vinylester composite (V (3 wt.

%) with the best compressive strength performance was estimated to be 3.77 kg CO<sub>2</sub>/kg and 4.29 kg CO<sub>2</sub>/kg, respectively. In both composite materials, the resin is the main hotspot, contributing 97%.



**Table 2:** Environmental impacts on the production of tincal reinforced resin composites.

Composite	CC (kg CO <sub>2</sub> )	ADF (MJ)	ODP x 10 <sup>3</sup> (g CFC-11) eq)	POP x 10 <sup>3</sup> (kg C <sub>2</sub> H <sub>4</sub> ) eq)	AP x 10 <sup>3</sup> (kg SO <sub>2</sub> eq)	EP (kg PO <sub>4</sub> eq)
P (0 wt.%)	3.7627	82.2068	0.5829	7.1465	15.6830	6.3685
P (1 wt.%)	3.7642	82.2261	0.5831	7.1470	15.7006	6.3717
P (2 wt.%)	3.7656	82.2454	0.5833	7.1476	15.7183	6.3749
P (3 wt.%)	3.7671	82.2647	0.5835	7.1481	15.7359	6.3781
V (0 wt.%)	4.2895	87.3614	0.3272	8.1065	17.9749	6.8149
V (1 wt.%)	4.2910	87.3806	0.3274	8.1071	17.9925	6.8181
V (2 wt.%)	4.2924	87.3999	0.3276	8.1076	18.0102	6.8213
V (3 wt.%)	4.2939	87.4192	0.3278	8.1082	18.0278	6.8245

CC: Climate change, ADF: Abiotic depletion (fossil fuels), ODP: Ozone layer depletion, POP: Photochemical oxidant potential, AP: Acidification potential, EP: Eutrophication potential, P: Polyester, V: Vinylester, 0-3 wt.%: resin tincal ratio.

When Table 2 is examined, it is seen that the environmental impacts of vinylester resin composites, except for ODP, are higher than the environmental impacts of polyester resin composites. It is seen that the contribution of accelerators, electricity, transportation, and tincal used in composite production to environmental effects is quite low. In this case, the environmental effects of bisphenol A epoxy-based vinylester resin (except for ODP) are observed to be higher than those of orthophthalic acid-based unsaturated polyester resin.

It was calculated that there is an increase in environmental effects with the increase of tincal ratio in polyester and vinylester resins, but this increase contributes less than 1% to the total effect. When Figure 5 and Table 2 are evaluated together, the compressive strength increases with the increase of tincal in the polyester resin and when 3 wt.% tincal is added to the resin. It has been determined that there is an increase of 0.12% in the climate change category, 0.07% in fossil resource consumption, 0.11% in ozone depletion, 0.02% in photochemical oxidation, 0.34% in acidification and 0.15% in eutrophication. The highest compressive strength and surface hardness values are obtained when 2 wt.% tincal is added to the vinylester resin. When this 2% change is examined in terms of environment, it was found that there is an increase of 0.10% in the climate change category, 0.07% in fossil resource consumption, 0.19% in ozone depletion, 0.02% in photochemical oxidation, 0.29% in acidification, and 0.14% in eutrophication.

## CONCLUSIONS

Increasing the tincal content in the polyester resin increases the compressive strength of the polyester composite. When 3 wt.% tincal is added to the polyester resin, the compressive strength increases by 14.6%. The highest compressive

strength is obtained when 2 wt.% tincal is added to the vinylester resin. When tincal has been evaluated according to the sample that is not reinforced, there is an increase of 4.2% depending on the change in the tincal reinforcement ratio. Depending on the tincal addition rate, the highest surface hardness increase is obtained when 2 wt.% tincal is added to the resins. While the surface hardness increase rate in the polyester composite is 4.1%, it is found at 3.6% in the vinylester sample. Tincal ore reinforcement increases Shore D hardness and density of the polyester composite (38). For all polyester composites, the first relaxation time is  $2.14 \cdot 10^{-4}$  s and the relaxation time is  $9 \cdot 10^{-7}$  s. It has been observed that the relaxation times of vinylester composites vary between  $10^{-4}$  and  $10^{-6}$  seconds. LCA results showed that the environmental impact of vinylester resin composites is higher than that of polyester resin composites, and there is a partial increase in the environmental impact of composites with tincal reinforcement. It is thought that the performance of the composites increases with the addition of tincal to the polyester and vinylester resin and this increase will tolerate the partial increase in the environmental effects of the composites caused by tincal.

## ACKNOWLEDGMENT

The authors thank the managers and employees of Kirka Boron Operations Directorate of Eti Maden Company, who provided the supply of tincal ore used in the study.

## REFERENCES

- Bai T, Wang D, Yan J, Cheng W, Cheng H, Shi SQ, et al. Wetting mechanism and interfacial bonding performance of bamboo fiber reinforced epoxy resin composites. *Composites Science and Technology* [Internet]. 2021 Sep [cited 2022 Nov 8];213:108951. Available from: <URL>.

2. Chen YH, Wu CH, Chen YC. Optimized condition for eco-friendly wood composites manufactured from castor oil-based polyurethane. *Construction and Building Materials* [Internet]. 2021 Nov [cited 2022 Nov 8];306:124789. Available from: [<URL>](#).
3. Teng K, Ni Y, Wang W, Wang H, Xu Z, Chen L, et al. Adjustable micro-structure, higher-level mechanical behavior and conductivities of preformed graphene architecture/epoxy composites via RTM route. *Composites Part A: Applied Science and Manufacturing* [Internet]. 2017 Mar [cited 2022 Nov 8];94:178–88. Available from: [<URL>](#).
4. Lin W, Shi QQ, Chen H, Wang JN. Mechanical properties of carbon nanotube fibers reinforced epoxy resin composite films prepared by wet winding. *Carbon* [Internet]. 2019 Nov [cited 2022 Nov 8];153:308–14. Available from: [<URL>](#).
5. Wang H, Yuan J, Zhu Z, Yin X, Weng Y, Wang Z, et al. High performance epoxy resin composites modified with multifunctional thiophene/ phosphaphenanthrene-based flame retardant: Excellent flame retardance, strong mechanical property and high transparency. *Composites Part B: Engineering* [Internet]. 2021 Dec [cited 2022 Nov 8];227:109392. Available from: [<URL>](#).
6. Petraşcu OL, Manole R, Pascu AM. The behavior of composite materials based on polyurethan resin subjected to uniaxial tensile test. *Materials Today: Proceedings* [Internet]. 2022 [cited 2022 Nov 8];62:2673–8. Available from: [<URL>](#).
7. Erturk AT, Yarar E, Vatanserver F, Sahin AE, Kilingel M, Alpay YO. A comparative study of mechanical and machining performance of polymer hybrid and carbon fiber epoxy composite materials. *Polymers and Polymer Composites* [Internet]. 2021 Nov [cited 2022 Nov 8];29(9\_suppl):S655–66. Available from: [<URL>](#).
8. Alpay Y, Uygur I, Kilincel M. On the optimum process parameters of infrared curing of carbon fiber-reinforced plastics. *Polymers and Polymer Composites* [Internet]. 2020 Jul [cited 2022 Nov 8];28(6):433–9. Available from: [<URL>](#).
9. Xu W, Wu X, Shi B. Toughening agent for melamine formaldehyde resin: A new method for recycling chrome shavings. *Polymer* [Internet]. 2022 Jun [cited 2022 Nov 8];253:124979. Available from: [<URL>](#).
10. Lakhari MT, Bai Y, Wong LS, Paul SC, Anggraini V, Kong SY. Mechanical and durability properties of epoxy mortar incorporating coal bottom ash as filler. *Construction and Building Materials* [Internet]. 2022 Jan [cited 2022 Nov 8];315:125677. Available from: [<URL>](#).
11. Luo C, Li J, Chen Z, Lin J, Chen L, He S. Improving the charge dissipating performance and breakdown strength of epoxy resin by incorporating polydopamine-coated barium titanate. *Materials Today Communications* [Internet]. 2022 Jun [cited 2022 Nov 8];31:103619. Available from: [<URL>](#).
12. Jia F, Fagbohun EO, Wang Q, Zhu D, Zhang J, Gong B, et al. Improved thermal conductivity of styrene acrylic resin with carbon nanotubes, graphene and boron nitride hybrid fillers. *Carbon Resources Conversion* [Internet]. 2021 [cited 2022 Nov 8];4:190–6. Available from: [<URL>](#).
13. Halim ZAA, Yajid MAM, Nurhadi FA, Ahmad N, Hamdan H. Effect of silica aerogel – Aluminium trihydroxide hybrid filler on the physio-mechanical and thermal decomposition behaviour of unsaturated polyester resin composite. *Polymer Degradation and Stability* [Internet]. 2020 Dec [cited 2022 Nov 8];182:109377. Available from: [<URL>](#).
14. Reuter J, Greiner L, Kukla P, Döring M. Efficient flame retardant interplay of unsaturated polyester resin formulations based on ammonium polyphosphate. *Polymer Degradation and Stability* [Internet]. 2020 Aug [cited 2022 Nov 8];178:109134. Available from: [<URL>](#).
15. Na T, Liu X, Jiang H, Zhao L, Zhao C. Enhanced thermal conductivity of fluorinated epoxy resins by incorporating inorganic filler. *Reactive and Functional Polymers* [Internet]. 2018 Jul [cited 2022 Nov 8];128:84–90. Available from: [<URL>](#).
16. Gangil B, Ranakoti L, Verma SK, Singh T. Utilization of waste dolomite dust in carbon fiber reinforced vinylester composites. *Journal of Materials Research and Technology* [Internet]. 2022 May [cited 2022 Nov 8];18:3291–301. Available from: [<URL>](#).
17. Feng T, Wang Y, Dong H, Piao J, Wang Y, Ren J, et al. Ionic liquid modified boron nitride nanosheets for interface engineering of epoxy resin nanocomposites: Improving thermal stability, flame retardancy, and smoke suppression. *Polymer Degradation and Stability* [Internet]. 2022 May [cited 2022 Nov 8];199:109899. Available from: [<URL>](#).
18. Boztoprak Y, Kartal İ. Bor Nitrür Partikülleriyle Takviyelendirilmiş Vinil Ester Matrisli Kompozitlerin Mekanik Özelliklerinin İncelenmesi. *El-Cezeri Fen ve Mühendislik Dergisi* [Internet]. 2019 Jan 31 [cited 2022 Nov 8]; Available from: [<URL>](#).
19. Orhan R, Aydoğmuş E, Topuz S, Arslanoğlu H. Investigation of thermo-mechanical characteristics of borax reinforced polyester composites. *Journal of Building Engineering* [Internet]. 2021 Oct [cited 2022 Nov 8];42:103051. Available from: [<URL>](#).
20. Yılmaz E, Arslan H, Subaşı S, Uğur LO, Bideci A. Geri Dönüştürülmüş Lastik Atık İkameli Poliüretan Dolgulu Kompozit Panellerin Yaşam Döngüsü Değerlendirmesi. *Düzce Üniversitesi Bilim ve Teknoloji Dergisi* [Internet]. 2018 Aug 1 [cited 2022 Nov 8];6(4):1224–33. Available from: [<URL>](#).
21. Yılmaz E, Aykanat B, Çomak B. Environmental life cycle assessment of rockwool filled aluminum sandwich facade panels in Turkey. *Journal of Building Engineering* [Internet]. 2022 Jun [cited 2022 Nov 8];50:104234. Available from: [<URL>](#).
22. Benli Yıldız N, Arslan H, Yılmaz E. Life Cycle Assessment of Building Materials: Literature Review. *JOR*. 2020;8(1):210–9.
23. La Rosa AD, Greco S, Tosto C, Cicala G. LCA and LCC of a chemical recycling process of waste CF-thermoset composites for the production of novel CF-thermoplastic

- composites. Open loop and closed loop scenarios. *Journal of Cleaner Production* [Internet]. 2021 Jul [cited 2022 Nov 12];304:127158. Available from: [<URL>](#).
24. La Rosa AD, Banatao DR, Pastine SJ, Latteri A, Cicala G. Recycling treatment of carbon fibre/epoxy composites: Materials recovery and characterization and environmental impacts through life cycle assessment. *Composites Part B: Engineering* [Internet]. 2016 Nov [cited 2022 Nov 12];104:17–25. Available from: [<URL>](#).
25. Li X, Lv X, Zhou X, Meng W, Bao Y. Upcycling of waste concrete in eco-friendly strain-hardening cementitious composites: Mixture design, structural performance, and life-cycle assessment. *Journal of Cleaner Production* [Internet]. 2022 Jan [cited 2022 Nov 12];330:129911. Available from: [<URL>](#).
26. Kousis I, Fabiani C, Pisello AL. Could a bio-resin and transparent pavement improve the urban environment? An in field thermo-optical investigation and life-cycle assessment. *Sustainable Cities and Society* [Internet]. 2022 Apr [cited 2022 Nov 12];79:103597. Available from: [<URL>](#).
27. Forcellese A, Marconi M, Simoncini M, Vita A. Life cycle impact assessment of different manufacturing technologies for automotive CFRP components. *Journal of Cleaner Production* [Internet]. 2020 Oct [cited 2022 Nov 12];271:122677. Available from: [<URL>](#).
28. Aydoğmuş E, Arslanoğlu H, Dağ M. Production of waste polyethylene terephthalate reinforced biocomposite with RSM design and evaluation of thermophysical properties by ANN. *Journal of Building Engineering* [Internet]. 2021 Dec [cited 2022 Nov 12];44:103337. Available from: [<URL>](#).
29. Aydoğmuş E, Arslanoğlu H. Kinetics of thermal decomposition of the polyester nanocomposites. *Petroleum Science and Technology* [Internet]. 2021 Jul 18 [cited 2022 Nov 12];39(13–14):484–500. Available from: [<URL>](#).
30. Aydoğmuş E. Biohybrid nanocomposite production and characterization by RSM investigation of thermal decomposition kinetics with ANN. *Biomass Conv Bioref* [Internet]. 2022 Oct [cited 2022 Nov 12];12(10):4799–816. Available from: [<URL>](#).
31. Aydoğmuş E, Dağ M, Yalçın ZG, Arslanoğlu H. Synthesis and characterization of waste polyethylene reinforced modified castor oil-based polyester biocomposite. *J of Applied Polymer Sci* [Internet]. 2022 Jul 15 [cited 2022 Nov 12];139(27). Available from: [<URL>](#).
32. Şahal H, Aydoğmuş E, Arslanoğlu H. Investigation of thermophysical properties of synthesized SA and nano-alumina reinforced polyester composites. *Petroleum Science and Technology* [Internet]. 2022 Aug 8 [cited 2022 Nov 12];1–17. Available from: [<URL>](#).
33. Demirel MH, Aydoğmuş E. Atik maske takviyeli polyester kompozit üretimi ve karakterizasyonu. İnönü Üniversitesi Sağlık Hizmetleri Meslek Yüksek Okulu Dergisi [Internet]. 2022 Jan 17 [cited 2022 Nov 12]; Available from: [<URL>](#).
34. Demirel MH, Aydoğmuş E. Waste Polyurethane Reinforced Polyester Composite, Production, and Characterization. *Journal of the Turkish Chemical Society Section A: Chemistry* [Internet]. 2022 Mar 26 [cited 2022 Nov 12];443–52. Available from: [<URL>](#).
35. Yanen C, Aydoğmuş E. Characterization of Thermo-Physical Properties of Nanoparticle Reinforced the Polyester Nanocomposite. *DÜFED*. 2021;10(2):121–32.
36. Finkbeiner M, Inaba A, Tan R, Christiansen K, Klüppel HJ. The New International Standards for Life Cycle Assessment: ISO 14040 and ISO 14044. *Int J Life Cycle Assessment* [Internet]. 2006 Mar [cited 2022 Nov 12];11(2):80–5. Available from: [<URL>](#).
37. Chard J, Basson L, Creech G, Jesson D, Smith P. Shades of Green: Life Cycle Assessment of a Urethane Methacrylate/Unsaturated Polyester Resin System for Composite Materials. *Sustainability* [Internet]. 2019 Feb 15 [cited 2022 Nov 12];11(4):1001. Available from: [<URL>](#).
38. Yanen C, Dağ M, Aydoğmuş E. Investigation of Thermophysical Properties of Colemanite, Ulexite, and Tincal Reinforced Polyester Composites. *European Journal of Science and Technology* [Internet]. 2022 May 3 [cited 2022 Nov 12]; Available from: [<URL>](#).

