



Wood anatomy of Aleppo pine (*Pinus halepensis* Miller) grown naturally in Turkey

Yağmur Biricik¹ , Ünal Akkemik^{2,*} 

¹⁾ Republic of Turkey Ministry of Agriculture and Forestry, Marmara Forestry Research Institute, Maslak-İstanbul, Turkey

^{2,*} Istanbul University-Cerrahpasa, Forestry Faculty, Forest Botany Department, Bahçeköy-Istanbul, Turkey

Corresponding author: uakkemik@istanbul.edu.tr

Abstract

Pinus halepensis Mill. (Aleppo pine) is the least grown pine species in Turkey with two small forests. A total of 18 wood samples, 6 samples from northern slope and 6 from southern slope of Sirtlandağı in Milas-Muğla and 6 samples from the forest in Yumurtalık-Adana were collected. Tracheid and ray dimensions were measured on the photos of thin wood sections. As result, diameters of the earlywood tracheids in Aleppo pine are similar in both Adana and Muğla, while diameters of latewoods are wider especially on north aspect of the site in Muğla than Adana. The reason for this difference may probably be that the annual precipitation in Muğla is twice higher than that in Adana. Supporting the effect of lower precipitation in Adana, tracheid lengths are shorter, and tracheid frequencies are higher for a safety water transportation. All comparisons with the woods from Spain and Greece may be evaluated that the growing site conditions in Turkey are more favorable for the species and may be used in plantations. Furthermore, wood features in both Turkish and Aleppo pine species are very similar and their separation is almost impossible.

Keywords: Aleppo pine, wood elements, Mediterranean climate zone, ecological wood anatomy.

Introduction

Five native pine species in Turkey (*Pinus sylvestris* L., *Pinus nigra* Arnold subsp. *pallasiana* (Lamb.) Holmboe, *Pinus brutia* Ten, *Pinus pinea* L. and *Pinus halepensis*) constitute great forests on a total area of 12,117,122.5 ha, including high and coppice forests in general forest areas of Turkey (OGM, 2013). Particularly *Pinus nigra*, *P. sylvestris* and *P. brutia* have valuable woods, while *P. pinea* is preferring for its cones. *P. halepensis* is not well-known in Turkey, because of having two very small stands.

In the native pine species sapwood is yellowish or reddish white, and their heartwood is reddish brown. Because of large amount of resin canals, they can be seen with naked eye. Generally, pine wood has medium weight ($D_{12}=0.52 \text{ g/cm}^3$), moderate shock resistance, high modulus of elasticity and bending resistance, and is a medium soft, easily processed, well glued, good nail holding

material. Pine wood is used as construction timber, lumber, bridge material that comes into contact with soil and water when impregnated, mine pole, wire pole, flag pole, fence stakes and sleepers in aircrafts, ship deck floorings, packing box making, paper and cellulose industry (Bozkurt and Erdin, 1997).

Pinus halepensis is the least grown pine species in Turkey with a total distribution area of 715 ha, including 465 ha normal and 250 ha damaged high forests (OGM, 2013). Its natural distribution area starts from Western Portugal and reaches the Eastern Mediterranean. Its main distribution is in the Western Mediterranean coasts, unlike *Pinus brutia*. It establishes forests between 0-1700 m in the Mediterranean basin (especially the Western Mediterranean). It grows on coastal dunes, on almost every soil type in hilly areas and especially on calcareous soils. In Turkey, there are local distribution areas between Adana-Kadirli, Milas-Bodrum, around İzmir-Urla and Aydın-Selçuk (Coode and Cullen, 1965). Aleppo pine which has a natural distribution in limited areas, is in the VU (vulnerable) hazard category according to the International Union for Conservation of Nature hazard categories.

It is an evergreen forest tree, 10-15 m tall, with a curved trunk, pointed in youth, with a scattered crown when old. The red brown - grayish brown bark of the trunk remains smooth and uncracked for a long time, later light gray barks are in the form of scales. Shoots are light gray in color. Buds are small and resin free. The needles, which are mostly double and sometimes triple, are light green - bright green colored and thin; 6-15 cm long, delicate and have fine teeth on the edges. Lengths of cones are 8-18 cm, narrow and conical. Cone has a long, curved and thick stalk, therefore the tips of cones point down, unlike red pine. Cone stalk is up to 1-2 cm in length. The apophysis protrudes in a horizontal direction. The cones are bright brown and easily distinguished from red pine trees with red-chestnut color and stalkless cones (Coode and Cullen, 1965; Akkemik, 2014).

Annual ring boundaries are distinct. The transition from earlywood to latewood is gradual to abrupt. They have thin walled resin canals. There is no helical thickening and axial parenchyma. Rays are heterogeneous and usually uniseriate, rarely biseriate, Ray height is 1-25 cell. Ray tracheids are generally dentate. Cross-field pitting is pinoid and number of pits per cross-field 1-4. It is difficult and almost impossible to distinguish from Turkish pine (Akkemik and Yaman, 2012).

Along with the studies on the properties of Aleppo pine wood, studies on the wood formation is associated with climate (Attolini et al., 1990; Borghetti et al., 1998; Luis et al., 2007; Luis et al., 2011a, 2011b; Sanchez-Salguero et al., 2010; Olivar et al., 2012; Pasho et al., 2012; Novak et al., 2013;) are also increasing. Regarding the Aleppo pine species, which has a very limited distribution in Turkey, the physical and mechanical properties of its wood were determined by Erten and Sözen (1997), but no study has been conducted on the anatomical features of this species in detail (As et al., 2002). The aim of this study is to determine the wood anatomical features of Aleppo pine that grows naturally in Turkey.

Materials and method

The wood samples were collected from two different growing areas where are Muğla-Milas and Adana-Yumurtalık (Fig. 1). These two native areas have very limited distribution of Aleppo pine in Turkey and have hot and dry summers and warm-rainy in winters. According to the information

given by the General Directorate of Meteorology from the measurements of the last 90 years between 1929-2019, in Muğla the annual mean temperature is 15.1 °C, annual precipitation is 1214.8 mm; in Adana, annual mean temperature is 19.1 °C and annual precipitation is 671.3 mm (MGM, 2020).



Figure 1. The sampling points from Muğla-Milas and Adana-Yumurtalık.

A total of 18 wood samples, 6 samples from northern slope and 6 from southern slope of Sırtlandağı in Milas-Muğla and 6 samples in Yumurtalık-Adana were collected. Cylindrical wood samples with a diameter of 2 cm (Fig. 2) from west direction of the trees were taken from 1.30 m height by using a professional drill (see Biricik and Akkemik, 2017). Furthermore, increment cores were extracted with an increment borer to find the ages of the sampled trees. Tree diameters were also measured by a caliper (Table 1).

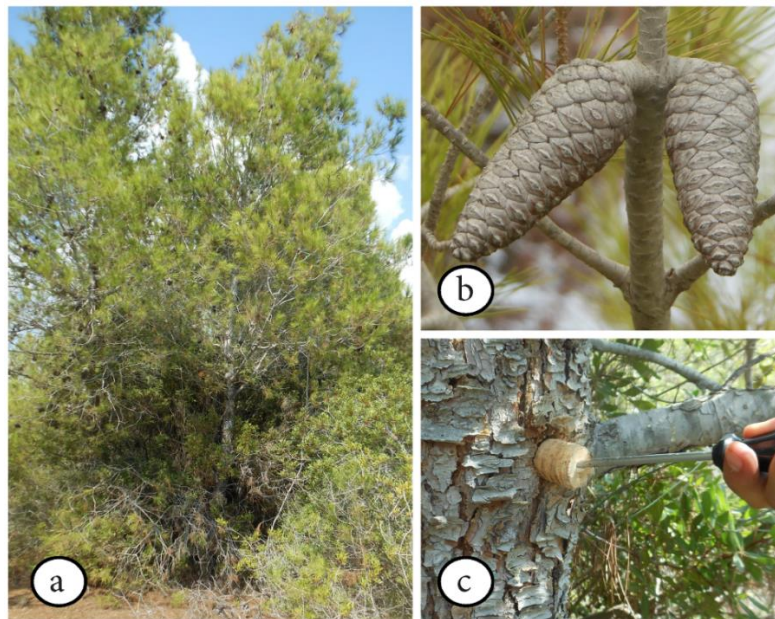


Figure 2. Photos of Aleppo pine; a) General view of a tree, b) cones, c) taking a wood specimen.

Table 1. The study areas, and some information about the sampled trees.

| Code | Aspect | Altitude (m) | Tree diameter (cm) | Tree height (m) | Tree age | Latitude (N) | Longitude (E) |
|------|--------|--------------|--------------------|-----------------|----------|--------------|---------------|
| MN1 | North | 50 | 26 | 10 | 19 | 37.174099 | 27.561788 |
| MN2 | North | 35 | 23 | 8 | 18 | 37.174172 | 27.561541 |
| MN3 | North | 32 | 20 | 9 | 19 | 37.174146 | 27.561462 |
| MN4 | North | 29 | 24 | 10 | 18 | 37.173969 | 27.560717 |
| MN5 | North | 39 | 30 | 12 | 24 | 37.174085 | 27.561072 |
| MN6 | North | 35 | 26 | 10 | 20 | 37.173805 | 27.560214 |
| MS1 | South | 36 | 22 | 8 | 16 | 37.162039 | 27.553871 |
| MS2 | South | 13 | 26 | 11 | 21 | 37.164361 | 27.550836 |
| MS3 | South | 35 | 30 | 13 | 25 | 37.162268 | 27.553276 |
| MS4 | South | 30 | 20 | 9 | 18 | 37.163721 | 27.577389 |
| MS5 | South | 32 | 22 | 8 | 20 | 37.164055 | 27.576290 |
| MS6 | South | 23 | 24 | 9 | 16 | 37.168850 | 27.573711 |
| AS1 | South | 0 | 27 | 12 | 22 | 36.741598 | 35.624809 |
| AS2 | South | 0 | 23 | 15 | 19 | 36.741607 | 35.624798 |
| AS3 | South | 1 | 24 | 16 | 22 | 36.742292 | 35.625202 |
| AS4 | South | 2 | 20 | 15 | 19 | 36.742166 | 35.625198 |
| AS5 | South | 1 | 28 | 12 | 25 | 36.742264 | 35.625235 |
| AS6 | South | 1 | 24 | 8 | 22 | 36.742173 | 35.625068 |

In the Laboratory of Tree-Ring Researches and Wood Anatomy of Faculty of Forestry Department of Forest Botany in Istanbul University-Cerrahpaşa, microscopic sections having a thickness of 30 micron were taken from three directions of the woods as transversal, radial and tangential sections by Leica Mikrotome SM 2010R, and microscope slides were prepared after standard chemical processes (Gartner and Schweingruber, 2013). Photos of wood elements from three different sections were taken with a Leica microscope and camera (DM2500), and all measurements and counts were performed on these photos by using the LAS Software of Leica System program (Fig. 3 and 4).

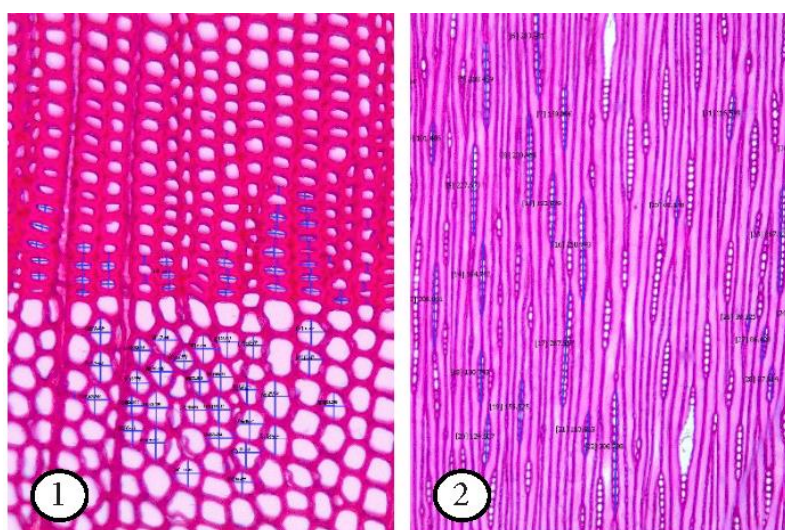


Figure 3. Measurements on (1) transversal and (2) tangential sections of Aleppo pine wood.

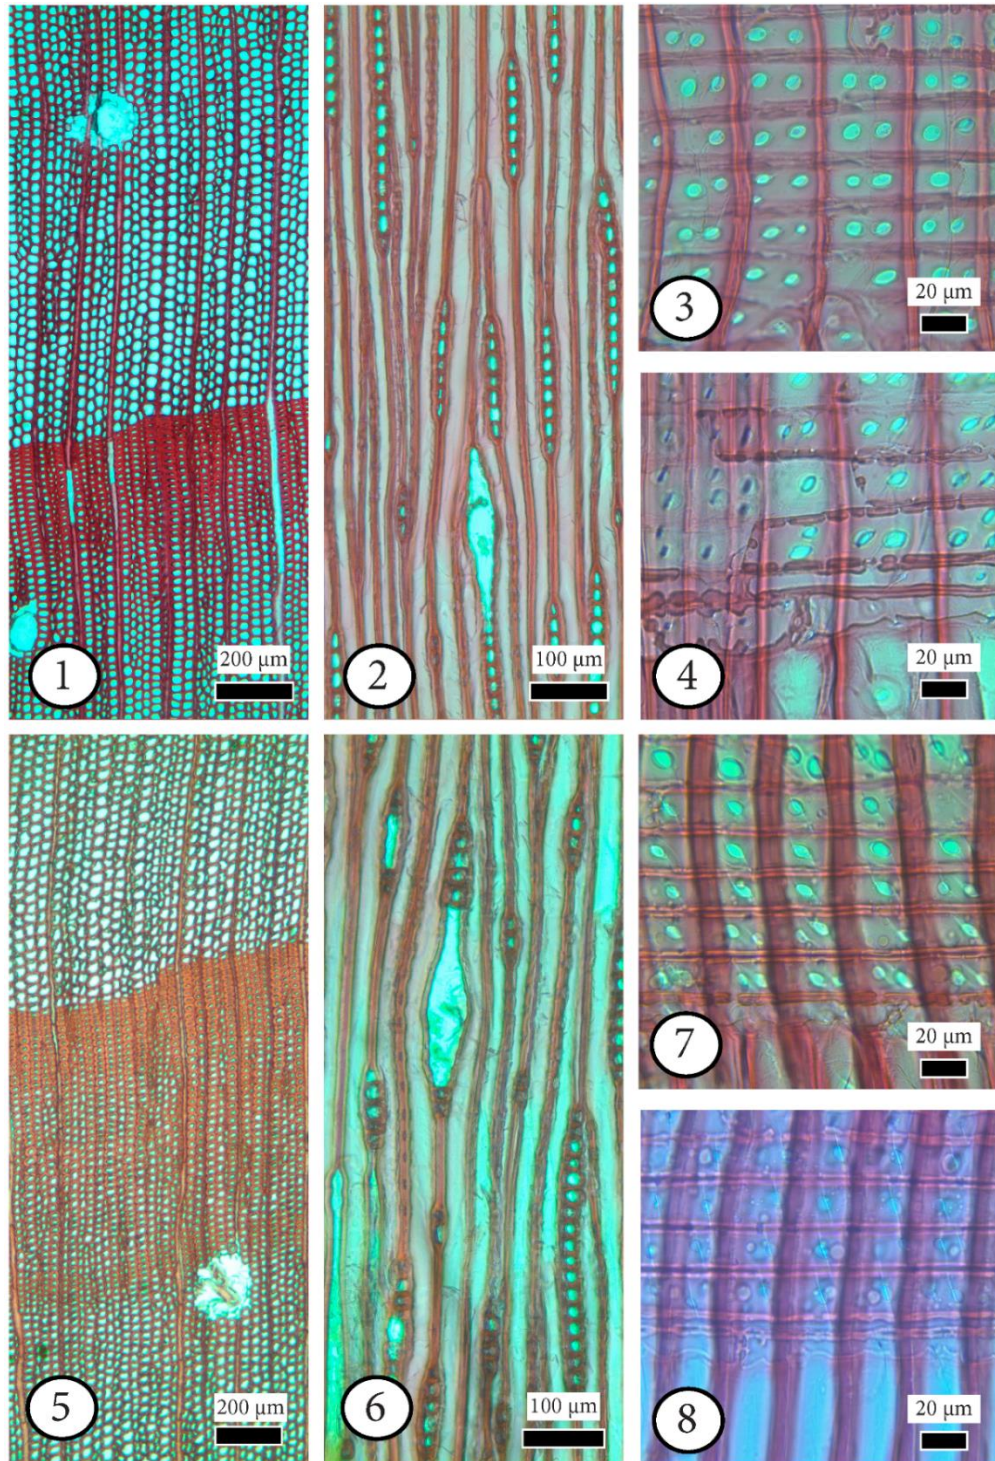


Figure 4. Wood thin sections of Aleppo pine. 1-4) Transversal, tangential and radial sections (Yumurtalık-Adana); 5-8) Transversal, tangential and radial sections (Milas-Muğla).

On the transversal sections of wood, tangential and radial lumen diameters and double wall thicknesses in both earlywood and latewood tracheids were measured. Tracheid number per square mm was counted. On the tangential sections of wood, ray heights and widths were measured; ray cell heights and ray number per mm were counted. Wood samples were separated into wood elements by Shultze maceration method (Sharma, 2005) and lengths of tracheids

obtained were measured. Based on suggestion of the IAWA Committee (2004), 30 measurements were performed for each feature in each sample, and finally a total of 7470 measurements were carried out.

By using the SPSS Program, similarities and differences between the sampling sites were determined. For this, Duncan test was performed in the measurements having a homogeneous of variance and normal distribution. Dunnett T3 test was performed in the measurements having normal distribution but no homogeneous of variance. Kruskal-Wallis Test was applied for the group with features that did not show normal distribution, and Mann-Whitney Test was applied for the pairs for those with differences.

Results

In the studied wood samples of Aleppo pine, average of tracheid tangential lumen diameter in earlywood was measured as 27.6 μm ; radial diameter was 28.5 μm . They are 18.5 μm and 7.7 μm in latewood (Table 2). The highest double cell wall thickness was measured as 9.17 μm in Adana, and the lowest one was 8.04 μm in northern slopes of Muğla. Average earlywood tracheid double wall thickness was measured as 4.11 μm in Adana, it was found higher with 6.18 μm in the north and 6.37 μm in the south slopes of Muğla. While the highest average tracheid length was obtained in the northern aspect of Muğla with 3975 μm (it was 3694 μm in the south aspect), the lowest value was found as 3038 μm in Adana. The highest number of tracheids per square mm was measured as 1232 in the woods from Adana (Table 2; Fig. 5).

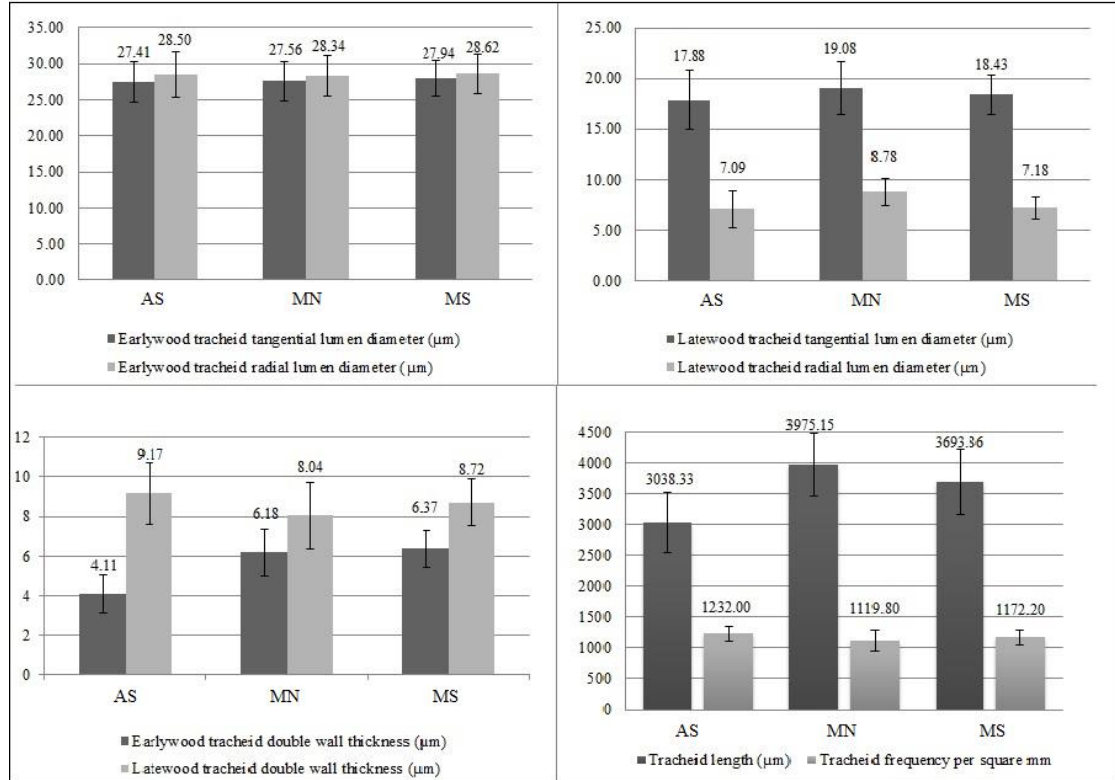


Figure 5. Tracheid properties of Aleppo pine (sample codes AS: south of Adana, MN: north slopes of Muğla, MS: south slopes of Muğla).

Table 2. Tracheid measurements and counts of Aleppo pine for different growing sides of Turkey.

| Code | Earlywood Tangential diameter (μm) | Earlywood Radial diameter (μm) | Earlywood Tracheid double wall thickness (μm) | Latewood Tangential diameter (μm) | Latewood Radial diameter (μm) | Latewood Tracheid double wall thickness (μm) | Tracheid length (μm) | Tracheid frequency per square mm |
|------------|---|---|--|--|--|---|-----------------------------------|----------------------------------|
| MN1 | 28.66 (± 3.41) | 30.81 (± 2.20) | 5.22 (± 1.01) | 18.48 (± 2.47) | 9.75 (± 1.28) | 7.05 (± 1.37) | 3990.96 (± 430.92) | 1058.40 (± 56.51) |
| MN2 | 28.49 (± 2.35) | 28.50 (± 1.81) | 5.80 (± 0.72) | 21.04 (± 2.60) | 9.18 (± 1.50) | 6.71 (± 1.06) | 3807.24 (± 437.29) | 1197.60 (± 166.16) |
| MN3 | 26.80 (± 1.75) | 28.54 (± 2.19) | 5.40 (± 0.81) | 17.10 (± 1.20) | 8.18 (± 0.69) | 7.53 (± 0.59) | 4123.82 (± 593.14) | 1293.60 (± 186.74) |
| MN4 | 27.58 (± 3.35) | 29.20 (± 3.52) | 6.74 (± 0.66) | 19.45 (± 1.59) | 8.54 (± 1.44) | 9.86 (± 1.64) | 3922.32 (± 426.83) | 919.20 (± 73.36) |
| MN5 | 26.44 (± 2.18) | 26.23 (± 2.44) | 7.50 (± 1.01) | 20.56 (± 2.59) | 8.45 (± 1.07) | 8.83 (± 1.67) | 4091.79 (± 553.58) | 1176.00 (± 91.74) |
| MN6 | 27.38 (± 2.12) | 26.77 (± 1.98) | 6.39 (± 0.95) | 17.82 (± 2.41) | 8.58 (± 1.17) | 8.28 (± 1.07) | 3914.76 (± 422.73) | 1074.00 (± 110.02) |
| MS1 | 28.83 (± 3.43) | 28.32 (± 4.06) | 6.58 (± 0.99) | 16.42 (± 1.95) | 7.38 (± 0.91) | 7.31 (± 0.90) | 3996.86 (± 524.34) | 1258.80 (± 110.34) |
| MS2 | 28.13 (± 2.06) | 28.10 (± 2.23) | 6.14 (± 0.90) | 18.12 (± 1.48) | 7.17 (± 0.88) | 8.93 (± 1.01) | 3731.34 (± 420.99) | 1062.00 (± 85.65) |
| MS3 | 28.56 (± 1.81) | 29.83 (± 2.41) | 7.10 (± 0.76) | 19.80 (± 1.43) | 8.35 (± 0.95) | 9.28 (± 1.20) | 3257.71 (± 299.67) | 1125.60 (± 90.30) |
| MS4 | 26.55 (± 1.75) | 27.74 (± 2.07) | 6.28 (± 0.92) | 18.50 (± 1.60) | 7.12 (± 0.87) | 8.58 (± 1.00) | 3659.85 (± 455.03) | 1173.60 (± 156.24) |
| MS5 | 28.22 (± 1.97) | 29.24 (± 2.53) | 6.19 (± 0.99) | 18.47 (± 1.76) | 6.82 (± 0.86) | 8.88 (± 0.95) | 3774.12 (± 406.18) | 1186.80 (± 104.68) |
| MS6 | 27.34 (± 2.64) | 28.48 (± 2.44) | 5.92 (± 0.70) | 19.29 (± 1.63) | 6.23 (± 0.68) | 9.31 (± 0.96) | 3743.29 (± 483.01) | 1226.40 (± 111.83) |
| AS1 | 26.82 (± 3.13) | 33.71 (± 4.91) | 3.64 (± 0.76) | 19.87 (± 2.60) | 8.43 (± 1.46) | 9.53 (± 1.70) | 2697.17 (± 399.51) | 1117.20 (± 83.99) |
| AS2 | 28.01 (± 2.42) | 32.64 (± 4.62) | 3.71 (± 0.90) | 19.23 (± 2.31) | 8.21 (± 1.71) | 8.50 (± 0.95) | 3050.67 (± 499.81) | 1256.40 (± 96.17) |
| AS3 | 27.44 (± 3.14) | 27.96 (± 2.50) | 4.66 (± 1.03) | 17.65 (± 2.86) | 7.06 (± 2.11) | 9.78 (± 1.94) | 3256.88 (± 402.34) | 1378.80 (± 80.89) |
| AS4 | 27.15 (± 2.98) | 26.97 (± 2.59) | 4.80 (± 0.93) | 16.35 (± 3.90) | 6.23 (± 1.32) | 8.53 (± 1.26) | 3158.62 (± 452.44) | 1226.40 (± 154.59) |
| AS5 | 28.24 (± 2.85) | 29.38 (± 3.31) | 3.78 (± 0.76) | 17.91 (± 1.65) | 7.14 (± 1.34) | 8.92 (± 1.23) | 3004.39 (± 389.43) | 1224.00 (± 77.36) |
| AS6 | 26.81 (± 2.29) | 27.34 (± 2.70) | 4.07 (± 0.66) | 16.25 (± 2.04) | 5.49 (± 0.85) | 9.75 (± 1.60) | 3062.27 (± 336.46) | 1189.20 (± 77.86) |

Table 3. Ray measurements and counts of Aleppo pine from different growing sides of Turkey.

| Code | Ray height (cell) | Ray height (μm) | Ray width (μm) | Ray frequency per mm |
|------|---------------------|------------------------------|-----------------------------|----------------------|
| MN1 | 8.40 (± 4.27) | 168.20 (± 71.26) | 25.45 (± 3.20) | 7.73 (± 1.20) |
| MN2 | 7.37 (± 3.27) | 168.53 (± 63.46) | 26.34 (± 2.48) | 7.53 (± 1.04) |
| MN3 | 7.03 (± 3.69) | 170.71 (± 69.89) | 25.70 (± 2.29) | 6.87 (± 1.04) |
| MN4 | 7.03 (± 3.55) | 166.98 (± 56.15) | 28.75 (± 2.61) | 8.27 (± 1.08) |
| MN5 | 8.37 (± 3.81) | 168.50 (± 58.44) | 25.39 (± 2.69) | 7.50 (± 0.90) |
| MN6 | 8.07 (± 3.93) | 164.51 (± 58.53) | 25.09 (± 2.57) | 7.37 (± 1.19) |
| MS1 | 8.43 (± 3.78) | 160.93 (± 65.17) | 25.39 (± 3.10) | 7.57 (± 1.04) |
| MS2 | 7.47 (± 3.47) | 164.25 (± 59.73) | 26.43 (± 2.88) | 7.27 (± 1.23) |
| MS3 | 7.27 (± 3.12) | 158.30 (± 56.83) | 25.67 (± 3.23) | 6.80 (± 1.10) |
| MS4 | 9.30 (± 4.36) | 163.91 (± 71.22) | 23.32 (± 2.58) | 7.50 (± 1.01) |
| MS5 | 7.63 (± 3.30) | 157.68 (± 65.16) | 22.89 (± 2.84) | 7.43 (± 1.19) |
| MS6 | 7.47 (± 3.30) | 160.71 (± 59.80) | 25.27 (± 2.22) | 7.70 (± 1.12) |
| AS1 | 7.77 (± 3.96) | 155.10 (± 70.51) | 20.97 (± 2.97) | 8.50 (± 0.94) |
| AS2 | 6.60 (± 3.20) | 131.50 (± 50.53) | 22.93 (± 2.80) | 7.70 (± 0.88) |
| AS3 | 7.07 (± 3.89) | 153.36 (± 79.11) | 25.70 (± 3.76) | 7.87 (± 0.90) |
| AS4 | 8.50 (± 4.74) | 156.79 (± 83.80) | 21.43 (± 2.12) | 10.47 (± 1.10) |
| AS5 | 8.27 (± 3.80) | 151.92 (± 66.16) | 20.61 (± 2.59) | 8.07 (± 1.01) |
| AS6 | 8.33 (± 4.05) | 155.34 (± 71.88) | 21.95 (± 2.29) | 8.50 (± 1.07) |

The ray cell heights are similar in all sites, when the ray widths are higher ($26.12 \mu\text{m}$) in Muğla, especially in the northern slopes. Average ray number per mm is 8.17 in Adana and 7.38 in the south slopes of Muğla (Fig. 6).

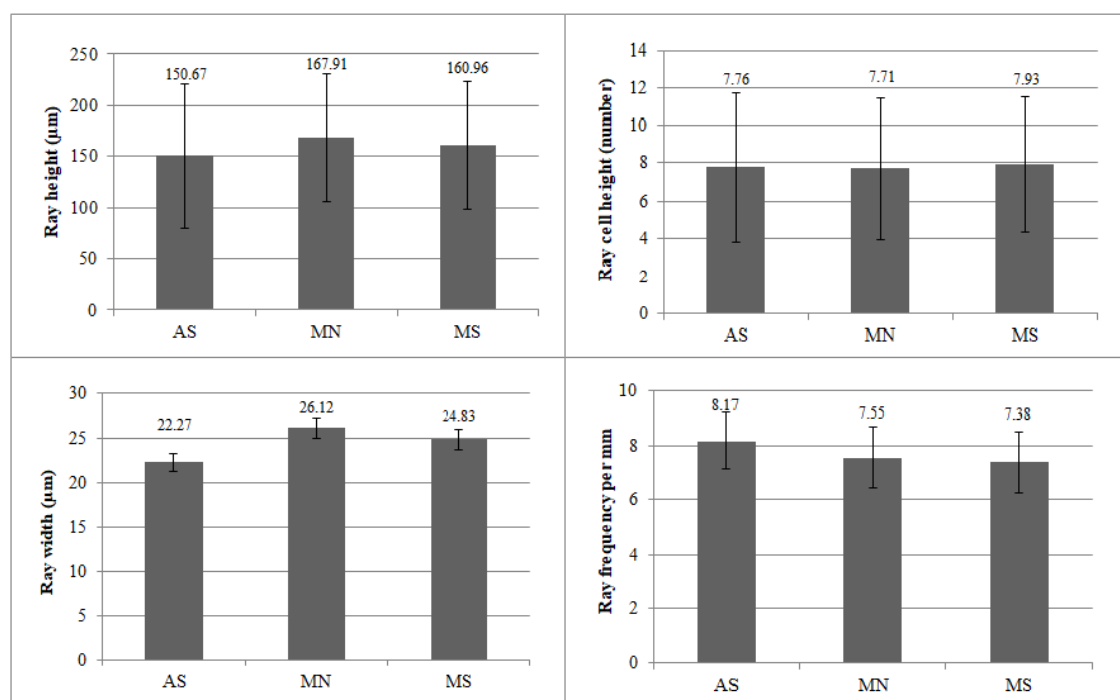


Figure 6. Ray properties of Aleppo pine.

The statistical results showed that wood features in three different growing sites are mostly similar with some important differences (Table 4). Particularly earlywood tracheid tangential and radial diameters fallen into the same group and no significant differences between them. Because they are the main water conducting elements, this result showed the presence of similar spring and early summer conditions in three sites.

Regarding the latewood tracheid diameters, while the sites in Adana and in south aspect of Muğla fall into the same group, the site in north aspect of Muğla shows a different group. This result indicated that some differences can be seen in summer conditions. Aspect in dry sites are important in respect of water storage and evaporation. Because north aspect relatively has lower evaporation and higher water storage, the water conducting elements (tracheids) showed a different group and their diameters are higher. On the contrary, in Adana and in south aspect in Muğla, tracheid diameters are lower and fallen into the same group. This result indicated that south aspect is drier than the north aspect of growing sites of Aleppo pine in Turkey.

Discussion

Lumen diameters of the earlywood tracheids in Aleppo pine are similar in both Adana and Muğla, while diameters of latewoods are wider in especially on north aspect of the site in Muğla than Adana. The reason for this difference may probably be that the annual precipitation in Muğla (1,215 mm) is two times higher than that in Adana (671 mm). Supporting the effect of lower precipitation in Adana, double wall thicknesses of the latewood tracheid are higher, tracheid lengths are longer, their frequencies are higher in Adana for a safety water transportation. On the other hand, heights and widths of rays are lower and ray frequencies are higher in Adana, as well.

Esteban et al. (2010) have studied wood anatomy of Aleppo pine from three Mediterranean region of Spain. In Inland Catalonia, Southern Spain and Balearic Islands, annual precipitation is 539 mm, 584 mm and 451 mm, respectively. The lengths of tracheids 583.55 μm , 632.07 μm , 659.76 μm ; lumen diameters 20.16 μm , 21.52 μm , 20.20 μm ; wall thicknesses 4.18 μm , 2.77 μm , 2.93 μm for earlywood tracheids respectively. In Turkey's Mediterranean region, precipitation is higher as 1215 mm in Muğla and 671 mm in Adana, and lengths of tracheids 3835 μm and 3038 μm ; lumen diameters 27.75 μm and 27.41 μm for earlywood, 18.76 μm and 17.88 μm for latewood; wall thicknesses 3.14 μm and 2.06 μm for earlywood, 4.19 μm and 4.59 μm for latewood tracheids, respectively (Fig. 3). Because of being more precipitation in Turkey, tracheid lengths are longer, lumen diameters are wider and wall thicknesses are thinner than those in Spain.

Pacheco et al. (2015) found average tracheid wall thickness 4.14 μm and lumen diameters 24.82 μm for Aleppo pine growing in the Middle Ebro Basin (Spain), which have an annual precipitation as 313 mm. Although precipitation is lower than Turkey, wood features are very similar to Turkish Aleppo pine woods. They also remarked that wet and warm late-winter and summer conditions were associated with wider wall thickness in Aleppo pine as Muğla compared with Adana.

Foti et al. (2018) studied tracheid length and wood density of Aleppo pine and their relations to cambial age and growth rate in Thessaloniki-Greece. They found average tracheid length 2550 μm (1250-3640 μm) for 21-23 ages. Their shorter lengths might depend on xeric climate conditions than those of Turkey. All comparisons with the woods from Spain and Greece may be evaluated that the growing site conditions in Turkey are more favorable for the species and may be used in plantations.

Table 4. Statistical results of wood features from three different sites and their comparison.

| | Earlywood tracheids tangential diameter ¹⁺⁺ | Earlywood tracheids radial diameter ¹⁺ | Latewood tracheids tangential diameter ¹⁺⁺ | Latewood tracheids radial diameter ² | Earlywood tracheids double wall thickness ¹⁺⁺ | Latewood tracheids double wall thickness ² | Tracheid number per square mm ¹⁺⁺ | Tracheid length ¹⁺ | Ray height ¹⁺ | Ray width ² | Ray cell height ² | Ray number per mm ² |
|------------------|--|---|---|---|--|---|--|-------------------------------|--------------------------|------------------------|------------------------------|--------------------------------|
| Adana | 27,41a | 28,50a | 17,88a | 7,09a | 4,11a | 9,17c | 1232,00b | 3038,33a | 150,67a | 22,27a | 7,76a | 8,17b |
| Muğla-North site | 27,56a | 28,34a | 19,07b | 8,78b | 6,18b | 8,04a | 1119,80a | 3975,15c | 167,90b | 26,12c | 7,71a | 7,54a |
| Muğla-South site | 27,94a | 28,62a | 18,43a | 7,18a | 6,37b | 8,72b | 1172,20a | 3693,86b | 160,96ab | 24,83b | 7,93a | 7,38a |

1= Normal distribution, + Variance homogenous (Duncan Test), ++ Variance no homogenous (Dunnett T3 test), 2= No normal distribution (The Kruskal-Wallis Test was applied within the group, and the Mann-Whitney Test was applied for the pair in those with a difference).

The species with the closest characteristics and habitat requirements to Aleppo pine is Turkish pine (*Pinus brutia* Ten.). Bozkurt et al. (1993) studied wood anatomy of Turkish pines grown in Datça and found diameters of tracheids as 40 µm, lumen widths 26.5 µm, cell wall thicknesses 6.8 µm, tracheid lengths 2880 µm for earlywood, 3210 µm for latewood. Furthermore, Ay (1993) determined diameters of tracheids as 44.16 µm, lumen widths 35.56 µm, cell wall thicknesses 4.7 µm, earlywood tracheid lengths 3230 µm and latewood tracheid lengths 3800 µm for woods of Turkish pines grown in Alanya. Diameters of wood elements are about the similar in both Turkish and Aleppo pines. Together with diameters, as stated by Schweingruber (1988) and Akkemik and Yaman (2012), growth rings, tracheid shapes, resin canals, cross-field pits and ray tracheids in both Turkish and Aleppo pine species are also very similar to each other, and their separation in wood identification is almost impossible.

Acknowledgement

This study was supported by General Directorate of Forestry of Turkey. We wish to thank our colleague, Umut Yüksel for his contributions to field works at Muğla and Adana. We also thank Prof. Dr. Orhan Sevgi for his help in statistical analysis.

References

- Akkemik, Ü., Yaman, B. (2012). Wood anatomy of eastern mediterranean species. Kessel Publishing House, Germany. ISBN: 978-3-941300-59-0.
- Akkemik, Ü. (ed.) (2014). Türkiye'nin doğal-egzotik ağaç ve çalıları I. OGM Yayınları, Ankara.
- As, N., Koç, H., Doğu, D., Atik, C. (2002). Türkiye'de yetişen endüstriyel öneme sahip ağaçların anatomik, fiziksel, mekanik ve kimyasal özellikleri. İÜ Orman Fakültesi Dergisi, B 51(1), 71-88.
- Ay, N. (1993). Internal morphological properties of *Pinus brutia* Ten. woods of Alanya. In: Proceedings of International Symposium on *Pinus brutia* Ten. 18-23 October 1993. Pp. 662-669.
- Attolini, M.R., Calvani, F., Galli, M., Nanni, T., Ruggiero, L., Schaer, E., Zuanni, F. (1990). The relationship between climatic variables and wood structure in *Pinus halepensis* Mill. Theoretical and Applied Climatology 41, 121-127.
- Biricik, Y., Akkemik, Ü. (2017). A mechanized technic to take wood samples from living trees. Turkish Journal of Forestry Research, 4(2), 152.
- Borghetti, M., Cinnirella, S., Magnani, F. (1998). Impact of long-term drought on xylem embolism and growth in *Pinus halepensis* Mill. Trees 12, 187-195.
- Bozkurt, Y., Erdin, N. (1997). Ağaç Teknolojisi, İstanbul Üniversitesi Orman Fakültesi Yayınları, İstanbul.
- Bozkurt, A.Y., Göker, Y., Erdin, N., As, N. (1993). Anatomical and technological properties of Brutian pine (*Pinus brutia* Ten.) grown in Datça, Turkey. In: Proceedings of International Symposium on *Pinus brutia* Ten. 18-23 October 1993. pp: 628-635.
- Coode, M.J.E., Cullen, J. (1965). *Pinus* L., in: Davis P.H. (ed.), Flora of Turkey and the East Aegean Islands 1. Edinburgh University Press, Edinburgh. 72-75.
- Erten, A. P., Sözen, M. R. (1997). Halep çamı (*Pinus halepensis* Mill.) odununun fiziksel ve mekanik özelliklerinin belirlenmesi. İç Anadolu Ormançılık Araştırma Enstitüsü Yayınları, Teknik Bülten Serisi 268, Ankara.

Esteban, L.G., Martin, J.A., Palacios, P., Fernandez, F.G., Lopez, R. (2010). Adaptive anatomy of *Pinus halepensis* trees from different Mediterranean environments in Spain. *Trees* 24, 19-30.

Foti, D., Passialis, C., Voulgaridis, E., Skaltsoyiannes, A., Tsaksira, M. (2018). Wood density and tracheid length of Aleppo pine (*Pinus halepensis* Mill.) grafts in relation to cambium age and growth rate. *Journal of Forest Science* 64(3), 101-107.

Gartner, H., Schweingruber, F.H. (2013). Microscopic preparation techniques for plant stem analysis. Kessel Publishing House, Germany. ISBN: 978-3-941300-76-7.

IAWA Committee (2004). IAWA List of microscopic features for softwood identification. Richter H.G., Grosser D., Heinz I., Gasson P.E. (eds.). *IAWA Journal* 25 (1), The Netherlands, 1-70.

Luis, M., Gricar, J., Cufar, K., Raventos, J. (2007). Seasonal dynamics of wood formation in *Pinus halepensis* from dry and semi-arid ecosystems in Spain. *IAWA Journal*, 28(4), 389-404.

Luis, M., Novak, K., Raventos, J., Gricar, J., Prislán, P., Cufar, K. (2011a). Climate factors promoting intra-annual density fluctuations in Aleppo pine (*Pinus halepensis*) from semiarid sites. *Dendrochronologia* 29, 163-169.

Luis, M., Novak, K., Raventos, J., Gricar, J., Prislán, P., Cufar, K. (2011b). Cambial activity, wood formation and sapling survival of *Pinus halepensis* exposed to different irrigation regimes. *Forest Ecology and Management* 262, 1630-1638.

MGM, 2020. <https://www.mgm.gov.tr/veridegerlendirme/il-ve-ilceler-istatistik>.

Novak, K., Luis, M., Raventos, J., Cufar, K. (2013). Climatic signals in tree-ring widths and wood structure of *Pinus halepensis* in contrasted environmental conditions. *Trees*, 27(4), 927-936.

OGM (2013). Orman Atlası. Orman Genel Müdürlüğü Yayınları, Ankara, 116.

Olivar, J., Bogino, S., Spiecker, H., Bravo, F. (2012). Climate impact on growth dynamic and intra-annual density fluctuations in Aleppo pine (*Pinus halepensis*) trees of different crown classes. *Dendrochronologia* 30, 35-47.

Pacheco, A., J. Camarero, J., Carrer, M. (2015). Linking wood anatomy and xylogenesis allows pinpointing of climate and drought influences on growth of coexisting conifers in continental Mediterranean climate. *Tree Physiology* 36, 502-512.

Pasho, E., Camarero, J.J., Vicente-Serrano, S.M. (2012). Climatic impacts and drought control of radial growth and seasonal wood formation in *Pinus halepensis*. *Trees* 26, 1875-1886.

Sanchez-Salguero, R., Navarro-Cerrillo, R.M., Camarero, J.J., Fernandez-Cancio, A. (2010). Drought-induced growth decline of Aleppo and maritime pine forests in south-eastern Spain. *Forest Systems*, 19(3), 458-469.

Schweingruber, F.H. (1988). *Anatomy of European Woods*. Paul Haupt. Switzerland.

Sharma, N.S. (2005). *Molecular cell biology*. International Scientific Publishing Academy, New Delhi, India.

Submitted: 29.09.2021

Accepted: 04.12.2021