

Study of the Sodiumborohydride Hydrolysis Reaction's Performance via a Kaolin-Supported Co-Cr Bimetallic Catalyst

*Makale Bilgisi / Article Info

Alındı/Received: 30.11.2023

Kabul/Accepted: 27.06.2024

Yayımlandı/Published: 01.10.2024

Kaolin Destekli Co-Cr Bimetalik Katalizör Yoluyla Sodyum Borhidrür Hidroliz Reaksiyonunun Performansının İncelenmesi

Erhan ONAT¹ , Selma EKİNCİ^{*2} 

¹ Bitlis Eren Üniversitesi, Organize Sanayi Bölgesi Meslek Yüksekokulu, Elektrik ve Enerji Bölümü, Bitlis, Türkiye

² Batman Üniversitesi Teknik Bilimler Meslek Yüksekokulu, Kimya ve Kimyasal İşleme Teknolojileri Bölümü, Batman, Türkiye

© Afyon Kocatepe Üniversitesi

Abstract

Hydrogen is an attractive source of energy because of its properties, which include superior quality, effectiveness, pureness, dependability, and sustainability. Technologies for producing and storing hydrogen are being developed in parallel with fuel cell development. Chemical storage of hydrogen in a metal hydride containing boron eliminates the problem of hydrogen transportation and storage. Through catalytic reactions, hydrogen stored in solid form in boron hydrides can be recovered. In this study, a novel developed Co-Cr bimetallic catalyst supported by kaolin, a natural mineral, was synthesized to be used for hydrogen production by hydrolysis of sodium boron hydride. The structural characteristics of the produced Co-Cr@Kaolin catalyst were ascertained by EDX, FT-IR, and SEM analyses. Next, the ideal conditions for the hydrolysis reaction of sodium borohydride (NaBH₄) catalyzed by Co-Cr@Kaolin were examined. These included the concentration of the catalyst, the amount of support material (kaolin), the amount of catalyst, and the concentration of NaBH₄. The optimal hydrolysis conditions were found to be 2.5 % NaOH concentration, 40 mg of catalyst, and 2% NaBH₄ concentration at 303 K. The maximum rate of hydrogen production was determined as 5007 mL g⁻¹ min⁻¹ under optimal conditions. After conducting hydrolysis operations at different temperatures to elucidate the reaction kinetics, it was found that the catalytic hydrolysis reaction was of the 0th order and that the reaction activation energy was 19.36 kJ mol⁻¹. The hydrogen production rate obtained as a result of the hydrolysis reaction accompanied by a Co-Cr catalyst was determined as 3166 mL g⁻¹ min⁻¹. It is therefore established that supporting kaolin to Co-Cr catalyst enhances its efficacy.

Keywords: Hydrogen; Kaolin; Sodium borohydride; Co-Cr@Kaolin; Supported Catalyst.

Öz

Hidrojen, üstün kalite, etkinlik, saflık, güvenilirlik ve sürdürülebilirlik gibi özellikleri nedeniyle cazip bir enerji kaynağıdır. Hidrojenin üretilmesi ve depolanmasına yönelik teknolojiler yakıt hücresi gelişimine paralel olarak geliştirilmektedir. Hidrojenin bor içeren bir metal hidrit içerisinde kimyasal olarak depolanması, hidrojenin taşınması ve depolanması sorununu ortadan kaldırır. Katalitik reaksiyonlar yoluyla bor hidritlerde katı halde depolanan hidrojen geri kazanılabilir. Bu çalışmada, sodyum bor hidrürün hidrolizi ile hidrojen üretiminde kullanılmak üzere doğal bir mineral olan kaolin ile desteklenen yeni geliştirilmiş Co-Cr bimetalik katalizörü sentezlendi. Üretilen Co-Cr@Kaolin katalizörünün yapısal özellikleri EDX, FT-IR ve SEM analizleri ile belirlendi. Daha sonra Co-Cr@Kaolin tarafından katalize edilen sodyum borohidrürün (NaBH₄) hidroliz reaksiyonu için ideal koşullar incelendi. Bunlar, katalizörün konsantrasyonunu, destek malzemesinin (kaolin) miktarını, katalizörün miktarını ve NaBH₄ konsantrasyonunu içermektedir. Optimum hidroliz koşullarının 303 K'de, % 2.5 NaOH konsantrasyonu, 40 mg katalizör ve % 2 NaBH₄ konsantrasyonu olduğu sonucuna varılmıştır. Optimum koşullar altında hidrojenin maksimum üretim hızının 5007 mL g⁻¹ dk⁻¹ olduğu belirlenmiştir. Reaksiyon kinetiğini aydınlatmak için farklı sıcaklıklarda hidroliz işlemleri yapıldıktan sonra katalitik hidroliz reaksiyonunun 0. mertebeden olduğu ve reaksiyonun aktivasyon enerjisinin 19.36 kJ mol⁻¹ olduğu bulunmuştur. Co-Cr katalizörü eşliğinde yapılan hidroliz reaksiyonu sonucunda elde edilen hidrojen üretim hızı ise 3166 mL g⁻¹ dk⁻¹ olarak belirlenmiştir. Bu nedenle, Co-Cr katalizörünün kaolin ile desteklenmesinin katalizörün etkinliğini artırdığı tespit edilmiştir.


Anahtar Kelimeler: Hidrojen; Kaolin; Sodyum borohidrid; Co-Cr@Kaolin; Destekli katalizör.

1. Introduction

Besides the gradual depletion of fossil fuels, burning them releases pollutants including unburned hydrocarbons, soot, odor, and carbon monoxide (CO), which are hazardous to human health and disturb the natural equilibrium of the environment (İzgi et al. 2017, Tarasova et al. 2022). In light of the concerning patterns of

environmental deterioration and the decrease of fossil fuel reserves, it is crucial to investigate alternatives to fossil fuels in order to promote the sustainable development of human civilization (Abdalla et al. 2018, Chen et al. 1997, Kumar and Das 2023). Scientific research indicates that hydrogen energy, which is becoming more and more popular as a fossil fuel substitute, is a clean and effective energy source. Hydrogen-powered fuel cells are

receiving a lot of attention as possible power sources for high-power applications and portable devices (such as energy generators) (Sartbaeva et al. 2008, Arzac et al. 2011, Koh et al. 2023). Hydrogen can be used as a fuel by means of systems called proton exchange membrane fuel cells (PEMFCs) (Ekinci 2020). In these cells, hydrogen is introduced into the system as a gas to produce electricity (Linden and Reddy 2001). The main argument in favor of using hydrogen as a fuel is the fact that it can be discovered in many different places. Carbon-based materials can be converted into hydrogen using thermochemical processes. Water can be converted into hydrogen using electrolysis, hydrolysis, and other processes. Solar energy can be converted into hydrogen using photoelectrochemical processes (Onat et al. 2024a, Onat et al. 2024b, Izgi et al. 2024). However, there are several drawbacks to using hydrogen as a fuel source (Acar and Dinçer 2019, Tutar and Eren 2011). These include the high expense of hydrogen fuel technology as well as the storage and gaseous hydrogen transportation. The chemical formation of hydrogen in boron compounds provides practically a whole solution to the transit and storage problem. (Sahiner and Demirci 2017, Lang et al. 2020). Its cost is significantly decreased by synthesizing the catalyst with loading-supported material. One of the most significant chemical hydrides is sodium borohydride (NaBH_4) due to its large (10.6 wt %) storage of hydrogen capability. Moreover, to have a high hydrogen storage capability, sodium borohydride also has a high hydrogen yield due to the hydrolysis that occurs when the hydrogen in its structure is separated from the water (Su et al. 2012, Demirci et al. 2010, Wee et al. 2006). Thermolysis or hydrolysis are two methods for dehydrogenating hydrogen contained in sodium borohydride (Sing 2022).



The catalyst can modify the reaction rate specified in Equation 1. This situation offers considerable advantages for employing hydrogen as a form of energy carrier by eliminating transit and storage problems (Özkar and Zahmakıran 2005). NaBH_4 undergoes an exothermic, spontaneous reaction known as self-hydrolysis. However, at ambient conditions, only 7-8 % of sodium borohydride produces hydrogen through self-hydrolysis. This value is insufficient for any fuel cell application. Consequently, the hydrolysis reaction can be accelerated by using metal or acid catalysts, particularly for sodium borohydride (Boran et al. 2013, Bai et al. 2006, Huang et al. 2021, Retnamma et al. 2011). Thus, a continuous hydrolysis reaction is possible at low temperature and pressure in the presence of metal catalysts (Kojima et al. 2011). In an alkaline solution, sodium borohydride does not burn. It also has various benefits, such as recycling byproducts. When a catalyst is used to hydrolyze NaBH_4 , hydrogen is released

spontaneously into the water (Su et al. 2012, Şahin et al. 2014a). In addition to releasing hydrogen from its structure, sodium borohydride also enables the recovery of hydrogen from the water structure, as shown in Equation 1. Thus, it becomes even more crucial to use it as a source of hydrogen (Tomasso et al. 2020).

Equation 1 can be used to generalize the hydrogen production from metal hydrides. The fact that this reaction is catalyst-controlled demonstrates how crucial the catalyst is for producing hydrogen (Strmcnik et al. 2016). Usually, valuable metals like Rh, Ru, Pd, and Pt are utilized as catalysts. Because these metals are expensive, metal combinations incorporating Co, Cu, Ni, and Mn are used instead, with increasing efficiency. Supported catalyst synthesis is another crucial technique for creating catalysts (Vesborg et al. 2015, Birry and Lasia 2004, Chen et al. 2013, Vračar and Conway 1990, Durst et al. 2014, Han et al. 2015, Kibsgaard and Jaramillo 2014, Huynh et al. 2013, Fernandes et al. 2009).

One common clay mineral, kaolin, is a significant non-metallic mineral source. After going through procedures including purifying and wroughting, kaolin is ground up and utilized to make pigment items and additives (Hubadillah et al. 2018, He et al. 2023). Kaolin is used widely in cement, ceramics, thermal energy storage materials, and other industrial areas due to its features of stable physical and chemical qualities, superior electrical isolation, high whiteness, a large area of a specific surface, high void proportion, and superior surface activation (Xie et al. 2019, Huang et al. 2017, Li et al. 2019).

This work demonstrates the synthesis of a novel material (Co-Cr@kaolin) that catalyzes the reaction of sodium borohydride hydrolysis. Following an identification of the Co-Cr@Kaolin catalyst's structure using EDX, FT-IR, and SEM investigations, the ideal conditions (kaolin amount, concentration of NaOH solution, catalyst amount, and concentration of NaBH_4) for the hydrolysis reaction were investigated. This work aims to produce an effective and dynamic catalyst with an affordable method for hydrogen production.

2. Materials and Method

2.1 Materials

Catalyst synthesis was carried out using an oven, burette, nitrogen tube, vacuum filtering device, and digital precision scale. For hydrolysis, a water bath, a gas measurement instrument, a stopwatch, and a digital precision scale were utilized.

2.2 Synthesis of Co-Cr catalyst

A chemical reduction technique was used to produce the Co-Cr catalyst according to the reference article (Fernandes et al. 2009). CoCl_2 and $\text{Cr}(\text{NO}_3)_3$ were

dissolved in water, and NaBH_4 was added as a reductant while the mixture was stirred quickly. The reduction of the Co and Cr cations into metal required an excessive number of borohydrides. After filtering and carefully washing with distilled water and ethanol, the black powder reaction result was dried at 323 K with a steady flow of N_2 . The $[\text{Cr}/(\text{Cr} + \text{Co})]$ molar ratio of the final Co-Cr catalyst powder could be changed by varying the molar concentration of $\text{Cr}(\text{NO}_3)_3$ in the aqueous solution.

2.3 Synthesis of Co-Cr@Kaolin catalyst

The impregnation method was utilized to support the Co-Cr catalyst with kaolin. The synthesis technique involved weighing and mixing the indicated amounts of Co-Cr catalyst for each experiment in a magnetic stirrer at 500 rpm for 30 minutes. Next, kaolin was added at a varied rate (70 %, 80 %, 90 %, and 95 %) in each trial. It was mixed once more for 20 hours at 500 rpm. Following that, it was reduced with sodium borohydride in the prescribed amounts. After the reduction, the catalyst was collected and vacuum-filtered before being dried for six hours at 60°C while surrounded by nitrogen. The catalyst, which was seen to be fully dry, was ground up and used to catalyze hydrolysis reactions of sodium borohydride.

2.4 Hydrolysis experiments

Experiments on hydrolysis were conducted in a jacketed tube with a magnetic stirrer at a speed of 600 rpm, at a temperature of 30 °C. Furthermore, a circulating water bath was employed to regulate the temperature since the system's temperature needed to be maintained consistently. An aqueous NaBH_4 solution was added to the reactor first, and then the catalyst was added. The produced hydrogen amount was then measured with a gas burette. The results were evaluated by drawing graphs for each experiment. Figure 1 shows an experimental working system of the hydrolysis reaction.

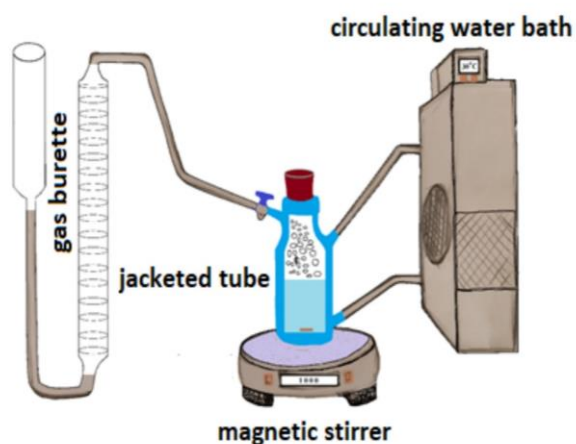


Figure 1. Hydrolysis reaction system

3. Results and Discussion

3.1 Catalyst characterization

Scanning electron microscopy (SEM), Fourier transform infrared spectroscopy (FT-IR), and Energy dispersion X-ray spectrometry (EDX) were used to characterize catalysts. SEM images of kaolin, Co-Cr catalysts, and Co-Cr@Kaolin catalysts are displayed in Figure 2.

The SEM picture of kaolin in Figure 2a demonstrates that it has a well-crystallized structure made up of hexagonal particles with varying thicknesses and diameters. According to the Co-Cr catalyst's morphology (Fig. 2(b)), the particles are spherical and small in size. Using NaBH_4 as a reducing agent during the catalyst manufacturing results in the fast reduction of Co ions, which prevents the creation of pertinent growth of particles. The Co-Cr@Kaolin catalyst has improved interparticle spacing without aggregation, which raises the catalyst's surface area that is actively catalyzing (Figure 2 (c)).

Identifying the compatibility of the catalyst content with the synthesized values is one of the crucial aspects of catalyst characterization. The catalyst for the Co-Cr system had 96 % Co and 4 % Cr. Figure 3(b) illustrates how these values are maintained in the catalyst content. The Co-Cr catalyst's EDX examination revealed the presence of Co and Cr metals (Figure 3 b). The Al and Si components in the kaolin's structure, which are visible in Figures 3(b) and 3(c), respectively, demonstrate that the kaolin binds to the catalyst (Bektaş et al. 2023, Onat and Ekinci, 2024).

The catalysts' FT-IR spectrum analysis results are displayed in Figure 4. The low-frequency portion of the FT-IR spectrum of Co-Cr reveals the cobalt ion-coordinated librational vibrations of molecules (Netskina et al. 2020). A potential metal-oxygen interaction is thought to be the cause of the band at 630 cm^{-1} (Nakamoto, 1963). While examining a Co(II) combination with pullulan, Miti et al. also discovered these bands (Sotiles et al. 2019). The peak at 1200 cm^{-1} is ascribed to vibrations of chromyl ($\text{Cr}=\text{O}$) (Weckhuysen et al. 1996, Trivedi et al. 2015). Cobalt (Co) and chromium (Cr) bands become increasingly prominent in the kaolin-supported catalyst structure, and the absorption bands of kaolin align with the stretching frequencies of OH groups between 3500 and 3750 cm^{-1} .

The peaks belonging to the Si-O, Al-OH, Si-O-Al, and Mg-Al-OH groups, in the structure of kaolin are seen at 1009, 912, 754, and 636 cm^{-1} , respectively, in the Co-Cr@kaolin spectrum (Tironia et al. 2012, Onat 2024). The SEM image in Figure 2 c is supported by this circumstance. Kaolin-supported catalyst surfaces crystallized more successfully and revealed themselves more clearly.

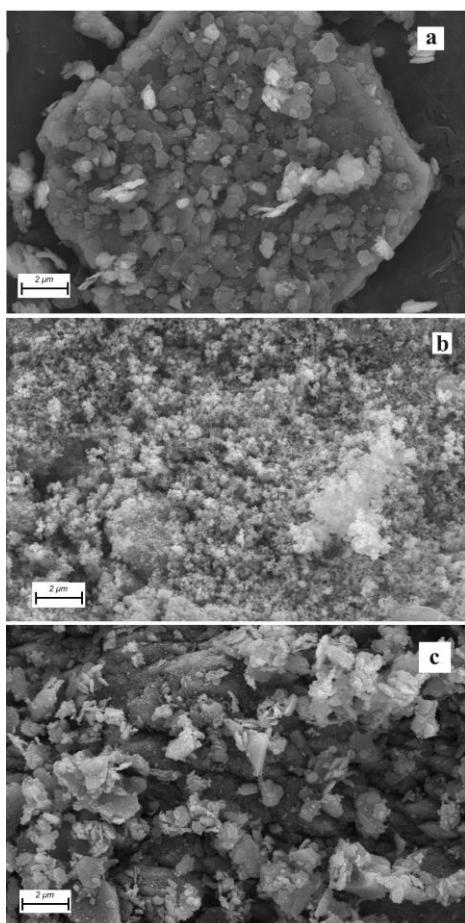


Figure 2. SEM images of a) kaolin b)Co-Cr catalyst c)Co-Cr@Kaolin catalyst.

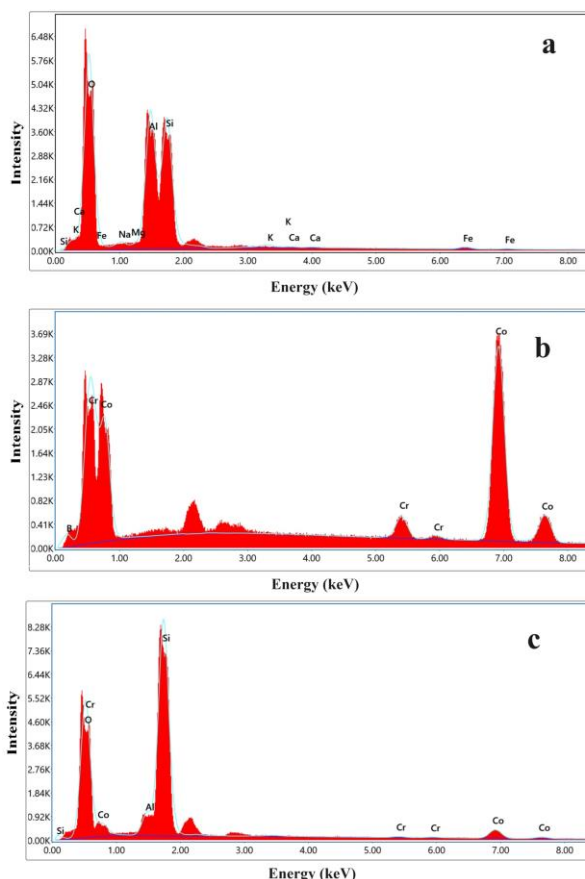


Figure 3. EDX analysis of a)Kaolin b)Co-Cr catalyst c)Co-Cr@Kaolin catalyst.

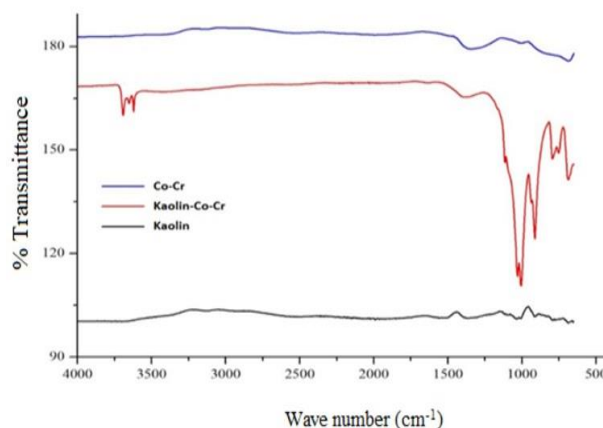


Figure 4. FT-IR analysis of Kaolin, Co-Cr catalyst, and Co-Cr@Kaolin catalyst.

3.2. Effect of kaolin ratio

The efficiency of the pure catalyst (Co-Cr) and the kaolin-supported Co-Cr catalyst (Co-Cr@Kaolin) were compared. $3166 \text{ mL g}^{-1} \text{ min}^{-1}$ was found to be the rate at which hydrogen is produced when a Co-Cr catalyst is present. Figure 5 displays data on hydrogen production during hydrolysis based on different kaolin ratios. Figure 5 illustrates that the maximum rate of production of hydrogen quantity was achieved when 90% kaolin was used. The rate at which hydrogen is produced in the presence of 90% kaolin was determined to be $4084 \text{ mL g}^{-1} \text{ min}^{-1}$. The following investigations were carried out using 90% kaolin, which was found to be the best value.

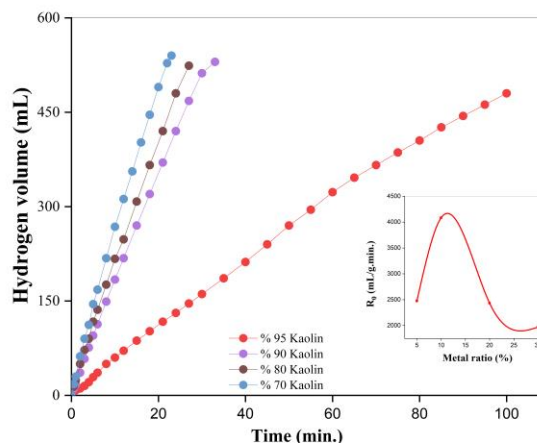


Figure 5. Hydrogen production rate as a function of kaolin ratio (50 mg catalyst, 30 °C, 5% NaOH, 2% NaBH₄).

3.3. Effect of NaOH ratio

NaOH concentration has a big impact on the process because the reaction of NaBH₄ hydrolysis can be suppressed without a catalyst by altering the pH of the reaction solution. In this study, four different starting NaOH solution concentrations (1%, 2.5%, 5%, and 7.5%) were used to quantify the volume of hydrogen produced by NaBH₄ hydrolysis. Figure 6 depicts the graph

showcasing these research findings. The greatest rate of generating hydrogen was found at a 2.5% concentration of NaOH, as illustrated in Figure 6. At this NaOH concentration, the rate of hydrogen production was calculated to be $5007 \text{ mL g}^{-1} \text{ min}^{-1}$. While the catalytic activity of the catalyst increased up to 2.5% NaOH concentration, after this concentration value, the catalyst's efficiency decreased with increasing NaOH concentration (Onat 2024, Izgi et al. 2019).

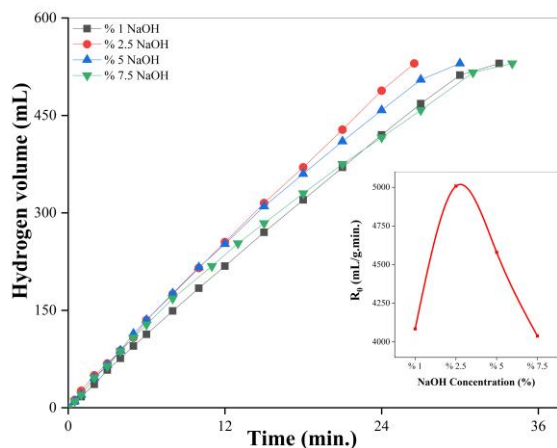


Figure 6. Hydrogen production rate as a function of mass percent of NaOH (50 mg catalyst, 30 °C, 2% NaBH₄).

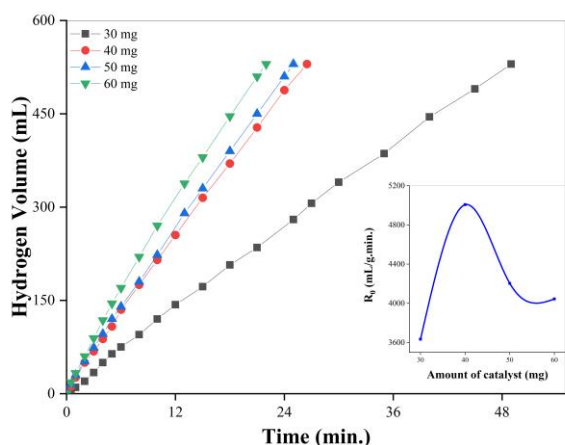


Figure 7. Hydrogen production rate as a function of catalyst amount (30 °C, 2.5% NaOH, 2% NaBH₄).

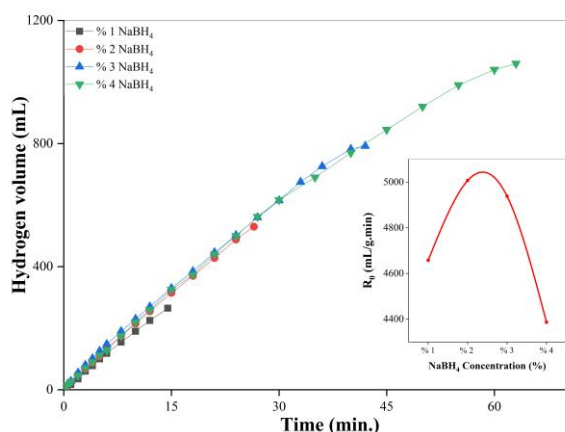


Figure 8. Hydrogen production volume as a function of NaBH₄ concentration (40 mg catalyst, 30 °C, 2.5% NaOH).

3.4. Effect of catalyst amount

To investigate the impact of catalyst amount on the rate of hydrogen production, experiments were conducted. Figure 7 shows the graph illustrating this impact. Even though the rate of hydrogen production increased when the catalyst dose was increased, the greatest rate of hydrogen generation was reached when 40 mg of catalyst was used. This demonstrates that using 40 mg of catalyst maintains the catalyst's surface area in contact with the substrate (Tian 2010, Onat and Izgi 2021).

3.5. Effect of Concentration of Sodium Borohydride

Several tests with constant catalyst and NaOH concentrations were conducted to determine the effects of varying NaBH₄ concentrations (1%, 2%, 3%, and 4% by mass) on the rate of hydrogen production. The effect of different NaBH₄ concentrations on the rate of hydrogen production is shown in Figure 8. As can be observed in Figure 8, the maximum rate of hydrogen generation was achieved when 2% by mass of NaBH₄ was used (Izgi et al. 2023). At this NaBH₄ concentration, the rate of hydrogen production was calculated to be $5007 \text{ mL g}^{-1} \text{ min}^{-1}$.

3.6. Effect of reaction temperature

Catalytic hydrolysis reactions of NaBH₄ with Co-Cr@Kaolin catalyst were conducted at 30, 40, 50, and 60 °C temperatures to examine the impact of temperature on the sodiumborohydride hydrolysis. Figure 9 depicts the hydrogen production rate as a function of time and various reaction temperatures. The Active Collision theory can be used to explain this circumstance. In other words, when the temperature rises, more interaction occurs between the particles (Patel and Miotello 2015). At 30 °C, the rate of hydrogen production is $5007 \text{ mL g}^{-1} \text{ min}^{-1}$. However, at 60 °C, the rate rises to $30325 \text{ mL g}^{-1} \text{ min}^{-1}$. This implies that when the temperature rises, the rate of reaction increases rapidly (Zhang et al. 2020).

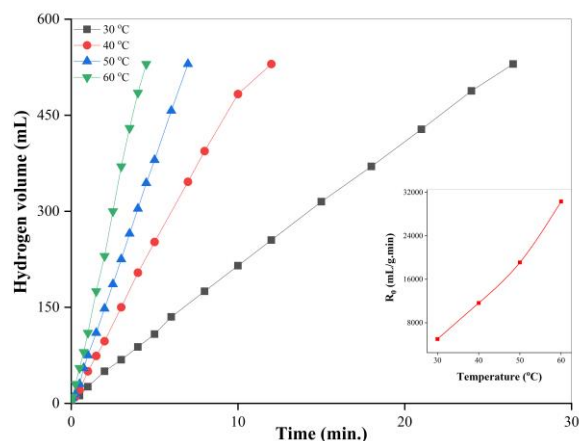


Figure 9. Hydrogen production rate as a function of temperature (40 mg cat., 2.5% NaOH, 2% NaBH₄).

3.7. Reaction Kinetics

Table 1 lists the kinetic values that were calculated using information on hydrogen production from hydrolysis experiments conducted at different temperatures. As a result, it has been proven that the reaction is of the 0th order, meaning that the catalyst affects the reaction's efficiency.

Table 1. Temperature-dependent kinetic data of NaBH₄ hydrolysis catalyzed by Co-Cr@Kaolin catalyst.

Temperature (°C)	Reac. Rate degree	Reac. Cons. (k)	HGR (mLg ⁻¹ min ⁻¹)	R ²
30	0. degree	0.019	5007	0.9992
40	0. degree	0.0427	11641	0.9939
50	0. degree	0.0638	19112	0.9998
60	0. degree	0.1052	30325	0.9985

In order to determine the reaction kinetics, the data of hydrogen production rates measured at different temperatures were evaluated in the Arrhenius equation (Equation 2).

$$\ln k = \ln A - \frac{E_a}{RT} \quad (2)$$

Here;

R is the universal gas constant (8.314 kJ K⁻¹mol⁻¹), k is the rate constant (min⁻¹), A is a constant known as the Arrhenius factor, and T is the absolute temperature (K). According to the Arrhenius equation, the plot of ln k versus 1/T was drawn (Figure 10). The activation energy (E_a) of the reaction was calculated from the slope of this graph as 19.36 kJ mol⁻¹ (Şahin et al. 2014b, Onat et al. 2021).

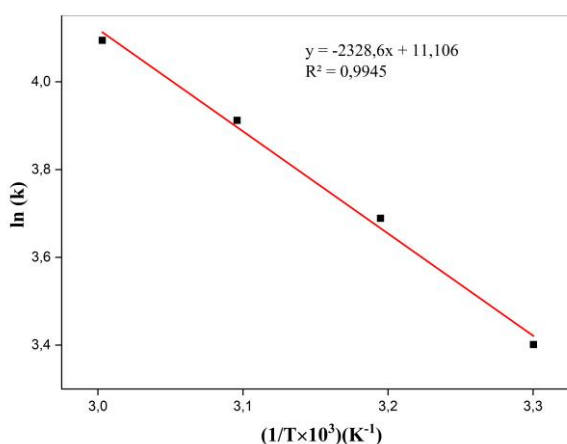


Figure 10. Arrhenius equation graph of hydrolysis reaction in the presence of Co-Cr@Kaolin catalyst.

4. Conclusion

This work investigated the catalytic activity of Co-Cr@kaolin in the hydrolysis of NaBH₄ to produce hydrogen. The ideal conditions for the maximum rate of hydrogen production were determined to be 40 mg of

catalyst, 2,5% NaOH, and 2% NaBH₄ by mass. With the Co-Cr@kaolin catalyst and the pure (Co-Cr) catalyst, the rates of hydrogen production via hydrolysis under these circumstances were found to be 5007 mL g⁻¹ min⁻¹ and 3166 mL g⁻¹ min⁻¹, respectively. Thus, adding kaolin to the pure catalyst enhanced its efficiency. A temperature-dependent increase in the rate of hydrogen generation was observed. Hydrogen production rates at 30 °C, 40 °C, 50 °C, and 60 °C were determined as 5007, 11641, 19112, and 30325 mL g⁻¹ min⁻¹, respectively. Investigations on characterization showed that kaolin improved the catalyst's effective surface without changing the catalyst's composition. Moreover, the Co-Cr@kaolin catalyst catalyzed the process at a low activation energy and produced a high amount of hydrogen.

Declaration of Ethical Standards

The authors declare that they comply with all ethical standards.

Credit Authorship Contribution Statement

Author-1: Conception, research, experimental analysis and reporting.

Author-2: Research, characterization, methodology and report.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data Availability Statement

All data generated or analyzed during this study are included in this published article.

5. References

- Abdalla M, Abdalla, Shahzad Hossain, Ozzan B. Nisfindy, Atia T. Azad, Mohamed Dawood, and Abul K. Azad. 2018. "Hydrogen production, storage, transportation and key challenges with applications: A Review." *Energy Conversion and Management* **165**:602-627. <https://doi.org/10.1016/j.enconman.2018.03.088>
- Acar, Canan, and İbrahim Dinçer. 2019. "Review and evaluation of hydrogen production options for better environment." *Journal of Cleaner Production* **218**:835-849. <https://doi.org/10.1016/j.jclepro.2019.02.046>
- Arzac, G. M, A. Fernández, A. Justo, B. Sarmiento, M. A, Jiménez, and M. M. Jiménez. 2011. "Optimized hydrogen generation in a semicontinuous sodium borohydride hydrolysis reactor for a 60 W-scale fuel cell stack." *Journal of Power Sources* **196**:4388-4395. <https://doi.org/10.1016/j.jpowsour.2010.10.073>
- Bai, Ying, Chuan Wu, Feng Wu, and Baolian Yi. 2006. "Carbon-supported platinum catalysts for on-site hydrogen generation from NaBH₄ solution." *Materials Matters* **60**:2236-2239. <https://doi.org/10.1016/j.matlet.2005.12.119>
- Bektaş, Hatice, Erhan Onat, Ömer Şahin, Sevilay Demirci, Orhan Baytar, and M. Sait İzgi. 2023. "Aktif karbon destekli ucuz ve kullanışlı katalizörün amonyak bor

- hidrolizinde incelenmesi." *Journal of Boron* **8(2)**:59-65.
<https://doi.org/10.30728/boron.1179156>
- Birry, L, and A. Lasia. 2004. "Studies of the hydrogen evolution reaction on raney nickel- molybdenum electrodes." *Journal of Applied Electrochemistry* **34**: 735–749.
<http://dx.doi.org/10.1023/B:JACH.0000031161.26544.6a>
- Boran, Asli, Serdar Erkan, Saim Ozkar, and İnci Eroglu. 2013. "Kinetics of hydrogen generation from hydrolysis of sodium borohydride on Pt/C catalyst in a flow reactor." *International Journal of Energy Research* **37**:443-448.
<https://doi.org/10.1002/er.3007>
- Chen, Chen, Binxu Lan, Kang Liu, Hongbo Wang, Xu Guan, Shijie Dong, and Ping Luo. 1997. "A novel aluminum/bismuth subcarbonate/salt composite for hydrogen generation from tap water." *Journal of Alloys and Compounds* **46**: 695-701.
<https://doi.org/10.1016/j.jallcom.2019.151733>
- Chen, W. F, C. H. Wang, K. Sasaki, N. Marinkovic, W. Xu, J. T. Muckerman, Y. Zhub and R. R. Adzic. 2013. "Highly active and durable nanostructured molybdenum carbide electrocatalysts for hydrogen production." *Energy & Environmental Science* **6**:943-951.
<https://doi.org/10.1039/C2EE23891H>
- Demirci, Ümit, O. Akdim, J. Andrieux, J. Hannauer, R. Chamoun, and P. Miele. 2010. "Sodium borohydride hydrolysis as hydrogen generator: Issues, state of the art and applicability upstream from a fuel cell." *Fuel Cells From Fundamentals to Systems* **10**:335-350.
<https://doi.org/10.1002/face.200800171>
- Durst, Julien, Christoph Simon, Frédéric Hasché and Hubert A. Gasteiger. 2014. "Hydrogen oxidation and evolution reaction kinetics on carbon supported Pt, Ir, Rh, and Pd electrocatalysts in acidic media." *Journal of The Electrochemical Society* **162**:190-203.
<https://iopscience.iop.org/article/10.1149/2.0981501jes>
- Ekinci, Arzu, 2020. "Hydrogen generation by hydrolysis of NaBH₄ with efficient Co–La–Mo–B catalyst for PEM fuel cells." *Kinetics and Catalysis* **61**: 589-594.
<http://dx.doi.org/10.1134/S0023158420040047>
- Fernandes R, N. Patel, and A. Miotello. 2009. "Hydrogen generation by hydrolysis of alkaline NaBH₄ solution with Cr-promoted Co–B amorphous catalyst." *Applied Catalysis B: Environmental* **92**:68-74.
<https://doi.org/10.1016/j.apcatb.2009.07.019>
- Han, Ali, Song Jin, Huanlin Chen, Hengxing Ji, Zijun Sun, and Pingwu Du. 2015. "A robust hydrogen evolution catalyst based on crystalline nickel phosphide nanoflakes on three-dimensional graphene/nickel foam: high performance for electrocatalytic hydrogen production from pH 0–14." *Journal of Materials Chemistry A* **3**:1941-1946.
<https://doi.org/10.1039/C4TA06071G>
- He, Jinfeng, Xin Zhang, Qiang Bai, Shibo Huang, Hao Chen, Chengjing Guo, Lingtao Zhu, and Bin Yang. 2023. "Surface modification to enhance the decarbonization performance of coal-series kaolin by triboelectric separation." *Applied Clay Science* **235**:106857.
<https://doi.org/10.1016/j.clay.2023.106857>
- Huang, Teng, Shaomin Lei, Yuanyuan Liu, Mengjiao Ji, and Yanming Fan. 2017. "Beneficiation and influencing factors of coal-series kaolin for the reduction of COD." *Applied Clay Science* **138**:4-39.
<https://doi.org/10.1016/j.clay.2016.12.032>
- Huang, Wenkai, Fuhua Xu, and Xiang Liu. 2021. "Superior hydrogen generation from sodium borohydride hydrolysis catalyzed by the bimetallic Co–Ru/C nanocomposite." *International Journal of Hydrogen Energy* **46**: 25376-25384.
<https://doi.org/10.1016/j.ijhydene.2021.05.083>
- Hubadillah, Siti Khadijah, M. H. D. Othman, Takeshi Matsuura, A. F. Ismail, M. A. Rahman, Zawati Harun, Juhana Jaafar, and Mikihiro Nomura. 2018. "Fabrications and applications of low cost ceramic membrane from kaolin: A comprehensive review." *Ceramics International* **44**: 4538-4560.
<https://doi.org/10.1016/j.ceramint.2017.12.215>
- Huynh, Keith, Krizia Napolitano, Ruiyao Wang, Philip G. Jessop, and Boyd R. Davis. 2013. "Indirect hydrolysis of sodium borohydride: Isolation and crystallographic characterization of methanolysis and hydrolysis by-products." *International Journal of Hydrogen Energy* **38**: 5775-5782.
<https://doi.org/10.1016/j.ijhydene.2013.03.011>
- İzgi, M.Sait, Orhan Baytar, Ömer Şahin, and Sabit Horoz. 2019. "Studies on catalytic behavior of Co–Cr–B/Al₂O₃ in hydrogen generation by hydrolysis of NaBH₄." *Digest Journal of Nanomaterials and Biostructures* **14**: 1005-1012.
- İzgi, M. Sait, Ömer Şahin, Erhan Onat, and Cafer Saka. 2020. "Epoxy-activated acrylic particulate polymer-supported Co–Fe–Ru–B catalyst to produce H₂ from hydrolysis of NH₃BH₃." *International Journal of Hydrogen Energy*, **45**:22638-22648.
<https://doi.org/10.1016/j.ijhydene.2020.06.048>
- İzgi, M. Sait, Erhan Onat, Hilal Çelik Kazici, and Ömer Şahin. 2023. "Hydrogen production through the cooperation of a catalyst synthesized in ethanol medium and the effect of the plasma." *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects* **45**: 8271-8284.
<https://doi.org/10.1080/15567036.2019.1677814>
- İzgi, M. Sait, Erhan Onat, Ömer Şahin, and Cafer Saka. 2024. "Green and active hydrogen production from hydrolysis of ammonia borane by using caffeine carbon quantum dot-supported ruthenium catalyst in methanol solvent by hydrothermal treatment." *International Journal of Hydrogen Energy* **51**: 180-192.
<https://doi.org/10.1016/j.ijhydene.2023.08.119>

- İzgi, M. Sait, Ömer Şahin, Erhan Onat, and Sabit Horoz. 2017. "Effect of Co-B catalyst synthesized in methanol on the hydrolysis of sodium borohydride." *Iğdır University Journal of Science and Technology* **7**: 151-160.
- Kibsgaard, Jakob, and Thomas F. Jaramillo. 2014. "Molybdenum phosphosulfide: An active, acid-stable, earth-abundant catalyst for the hydrogen evolution reaction." *Angewandte Chemie* **53**:14433-14437. <https://doi.org/10.1002/anie.201408222>
- Koh, Jae Seon, Do Hoon Kim, Se Hyeok Lee, and Min Soo Kim. 2023. "Hydrogen generation system for fuel cells based on high pressure hydrolysis of solid-state sodium borohydride." *Energy Conversion and Management* **281**: 116850. <https://doi.org/10.1016/j.enconman.2023.116850>
- Kojima, Yoshitsugu, Ken-ichirou Suzuki, Kazuhiro Fukumoto, Megumi Sasaki, Toshio Yamamoto, Yasuaki Kawai, and Hiroaki Hayashi. 2011. "Hydrogen generation using sodium borohydride solution and metal catalyst coated on metal oxide." *International Journal of Hydrogen Energy* **27**: 1029-1034. [https://doi.org/10.1016/S0360-3199\(02\)00014-9](https://doi.org/10.1016/S0360-3199(02)00014-9)
- Kumar Mamleshwar, and Taraknath Das. 2023. "Hydrogen generation from metal chloride doped sodium-borohydride by thermolysis at low temperature: The effect of material preparation methods." *Journal of Alloys and Compounds* **944**:169173. <https://doi.org/10.1016/j.jallcom.2023.169173>
- Lang, Chengguang, Yi Jia, and Xiangdong Yao. 2020. "Recent advances in liquid-phase chemical hydrogen storage." *Energy Storage Materials* **26**:290-312. <https://doi.org/10.1016/j.ensm.2020.01.010>
- Li, Xiaobin, Hong-yang Wang, Qiu-sheng Zhou, Tian-gui Qi, Gui-hua Liu, Zhi-hong Peng, Yi-lin Wang. 2019. "Efficient separation of alumina and silica in reduction-roasted kaolin by alkali leaching." *Transactions of Nonferrous Metals Society of China* **29**: 416-423. [https://doi.org/10.1016/S1003-6326\(19\)64951-4](https://doi.org/10.1016/S1003-6326(19)64951-4)
- Linden D., and Reddy, T.B., 2001. Handbook of Batteries and Fuel Cells, Kiehne H.A. (editor), Marcel Dekker Incorporation, 226-229.
- Mitić, Žarko, Goran M. Nikolić, Milorad Cakić, Goran S. Nikolić, Slavoljub Živanović, Sanja Mitić, and Stevo Najman, 2018. "Synthesis, spectroscopic and structural characterization of Co(II)-pullulan complexes by UV-Vis, ATR-FTIR, MALDI-TOF/TOF MS and XRD." *Carbohydrate Polymers* **200**: 25-34. <https://doi.org/10.1016/j.carbpol.2018.07.032>
- Nakamoto, Kazuo. 1963. Infrared spectra of Inorganic and Coordination Compounds. 2nd ed. New York: John Wiley and Sons.
- Netskina, Olga V, Alena A. Pochtar, Oxana V. Komova, and Valentina I. Simagina. 2020. "Solid-State NaBH₄ composites as hydrogen generation material: Effect of thermal treatment of a catalyst precursor on the hydrogen generation rate." *Catalysts* **10**: 201-213. <http://dx.doi.org/10.3390/catal10020201>
- Onat, Erhan, 2024. "Synthesis of a cobalt catalyst supported by graphene oxide modified perlite and its application on the hydrolysis of sodium borohydride." *Synthetic Metals* **306**: 117621. <https://doi.org/10.1016/j.synthmet.2024.117621>
- Onat, Erhan, Sabri Cevik, Ömer Şahin, Sabit Horoz, and M. Sait Izgi. 2021. "Investigation of high catalytic activity catalyst for high hydrogen production rate: Co-Ru@MOF." *Journal of the Australian Ceramic Society* **57**:1389-1395. <http://dx.doi.org/10.1007/s41779-021-00643-9>
- Onat, Erhan, and Selma Ekinci. 2024. "A new material fabricated by the combination of natural mineral perlite and graphene oxide: Synthesis, characterization, and methylene blue removal." *Diamond and Related Materials* **143**:110848. <https://doi.org/10.1016/j.diamond.2024.110848>
- Onat, Erhan, and M. Sait Izgi, 2021. "Hydrogen generation by hydrolysis of ammonia borohydride using the Nano-Bimetallic catalyst." *International Journal of Chemistry and Technology* **5(1)**: 1-5. <http://dx.doi.org/10.32571/ijct.785497>
- Onat, Erhan, M. Sait İzgi, Ömer Şahin, and Cafer Saka. 2024a. "Nickel/nickel oxide nanocomposite particles dispersed on carbon quantum dot from caffeine for hydrogen release by sodium borohydride hydrolysis: Performance and mechanism." *Diamond and Related Materials* **141**:110704. <https://doi.org/10.1016/j.diamond.2023.110704>
- Onat, Erhan, M. Sait İzgi, Ömer Şahin, and Cafer Saka. 2024b. "Highly active hydrogen production from hydrolysis of potassium borohydride by caffeine carbon quantum dot-supported cobalt catalyst in ethanol solvent by hydrothermal treatment." *International Journal of Hydrogen Energy* **51**: 362-375. <https://doi.org/10.1016/j.ijhydene.2023.08.176>
- Özkar, Saim, and Mehmet Zahmakıran. 2005. "Hydrogen generation from hydrolysis of sodium borohydride using Ru(0) nanoclusters as catalyst." *Journal of Alloys and Compounds* **404-406**: 728-731. <https://doi.org/10.1016/j.jallcom.2004.10.084>
- Patel Nainesh, and Antonio Miotello. 2015. "Progress in Co-B related catalyst for hydrogen production by hydrolysis of boron-hydrides: A review and the perspectives to substitute noble metals." *International Journal of Hydrogen Energy* **40(3)**: 1429-1464. <https://doi.org/10.1016/j.ijhydene.2014.11.052>

- Retnamma, Rajasree, Augusto Q. Novais, and C.M. Rangel. 2011. "Kinetics of hydrolysis of sodium borohydride for hydrogen production in fuel cell applications: A review." *International Journal of Hydrogen Energy* **36(16)**: 9772-9790.
<https://doi.org/10.1016/j.ijhydene.2011.04.223>
- Sartbaeva, Asel, Vladimir L. Kuznetsov, Stephen Wells, and Peter Edwards. 2008. "Hydrogen nexus in a sustainable energy future." *Energy & Environmental Science* **1**: 79-85.
<http://dx.doi.org/10.1039/b810104n>
- Sing, Rasmeeet. 2022. "Reversible chemical hydrogen storage in borohydrides via thermolysis and hydrolysis: recent advances, challenges, and perspectives." *International Journal of Hydrogen Energy* **47**:26549-26573.
<https://doi.org/10.1016/j.ijhydene.2021.10.022>
- Strmcnik, Dusan, , Pietro Papa Lopes, Bostjan Genorio, Vojislav R. Stamenkovic, and Nenad M. Markovic. 2016. "Design principles for hydrogen evolution reaction catalyst materials." *Nano Energy* **29**: 29-36.
<https://doi.org/10.1016/j.nanoen.2016.04.017>
- Sotiles, Anne Raquel, Fernando Massarotti, J. C.O. Pires, M. E. F. Ciceri, and C.R.B. Parabocz, 2019. "Cobalt complexes: Introduction and spectra analysis." *Orbital - The Electronic Journal of Chemistry* **11**: 349-354.
<http://dx.doi.org/10.17807/orbital.v11i6.1242>
- Su, Chia Chi, Ming Chun Lu, Shu Ling Wang, and Yao-Hui Huang. 2012. "Ruthenium immobilized on Al₂O₃ pellets as a catalyst for hydrogen generation from hydrolysis and methanolysis of sodium borohydride." *RSC Advances* **2**: 2073-2079.
<https://doi.org/10.1039/c2ra01233b>
- Şahin, Ömer, Orhan Baytar, Fevzi Hansu, and Cafer Saka. 2014a. "Hydrogen generation from hydrolysis of sodium borohydride with Ni (0) catalyst in dielectric barrier discharge method. Energy Sources, Part A: Recovery." *Utilization, and Environmental Effects* **36(17)**: 1886-1894.
<http://dx.doi.org/10.1080/15567036.2011.555442>
- Şahin, Ömer, Fevzi Hansu, Cafer Saka, and Orhan Baytar. 2014b. "Hydrogen generation from NaBH₄ solution with the high-performance Co (0) catalyst using a cold plasma method. Energy Sources, Part A: Recovery." *Utilization, and Environmental Effects* **36(14)**:1578-1587.
<http://dx.doi.org/10.1080/15567036.2011.555443>
- Şahiner, Nurettin, and Şahin Demirci. 2017. "Natural microgranular cellulose as alternative catalyst to metal nanoparticles for H₂ production from NaBH₄ methanolysis." *Applied Catalysis B: Environmental* **202**: 199-206.
<https://doi.org/10.1016/j.apcatb.2016.09.028>
- Tarasova, Nataliia, Anzhelika Bedarkova, Irina Animitsa, Ekaterina Abakumova, Ksenia Belova, and Hala Kreimesh. 2022. "Novel high conductive ceramic materials based on two-layer perovskite BaLa₂In₂O₇." *International Journal of Hydrogen Energy* **47**:17285-17312.
<https://doi.org/10.3390/ijms232112813>
- Tian, Hongjing, Qingjie Guo, and Dongyan Xu, D. 2010. "Hydrogen generation from catalytic hydrolysis of alkaline sodium borohydride solution using attapulgite clay-supported Co-B catalyst." *Journal of Power Sources* **195**: 2136-2141.
<http://dx.doi.org/10.1016/j.jpowsour.2009.10.006>
- Tironia, Alejandra, M. A. Trezzaa, E. F. Irassara, and A. N. Scian. 2012. "Thermal treatment of kaolin: effect on the pozzolanic activity." *Procedia Material Science* **1**: 343-350.
<http://dx.doi.org/10.1016/j.mspro.2012.06.046>
- Trivedi, Mahendra Kumar, R. M. R. Tallapragada, A. Branton, D. Trivedi, G. Nayak, O. Latiyal, and S. Jana. 2015. "Characterization of physical, thermal and structural properties of chromium (VI) oxide powder: Impact of biofield treatment." *Powder Metallurgy & Mining* **4**: 1000128.
<http://dx.doi.org/10.4172/2168-9806.1000128>
- Tomasso, Camille Jubert, Anne L. Pham, Tracy M. Mattox, and Jeffrey J. Urban. 2020. "Using additives to control the decomposition temperature of sodium borohydride." *Journal of Energy and Power Technology* **2**: 009.
<http://dx.doi.org/10.21926/jept.2002009>
- Tutar, Filiz, and Mehmet Eren. 2011. "Energy of the future: Hydrogen economy and Turkey." *International Journal of Economic and Administrative Studies* **6**:1-26.
<https://doi.org/10.18092/ijeas.38647>
- Weckhuysen, Bert M, Israel E. Wachs, and Robert A. Schoonheydt. 1996. "Surface chemistry and spectroscopy of chromium in inorganic oxides." *Chemical Reviews* **96**: 3327-3339.
<https://doi.org/10.1021/cr940044o>
- Wee, Jung-Ho, Kwan-Young Lee, and Sung Hyun Kim. 2006. "Sodium borohydride as the hydrogen supplier for proton exchange membrane fuel cell systems." *Fuel Process Technology* **87**: 811-819.
<http://dx.doi.org/10.1016/j.fuproc.2006.05.001>
- Xie, Xiaokang, Niu Sanxin, Miao Yang, Gao Xiang, Cheng Longsheng, Gao Feng. 2019. "Preparation and properties of resin coated ceramic proppants with ultralight weight and high strength from coal-series kaolin." *Applied Clay Science* **183**: 105364.
<https://doi.org/10.1016/j.clay.2019.105364>
- Vračar, L. J. and B. E. Conway, 1990. "Temperature dependence of electrocatalytic behaviour of some glassy transition metal alloys for cathodic hydrogen evolution in water electrolysis." *International Journal of Hydrogen Energy* **15**: 701-713.
[https://doi.org/10.1016/0360-3199\(90\)90001-F](https://doi.org/10.1016/0360-3199(90)90001-F)

Vesborg, Peter C. K. Brian Seger, and Ib Chorkendorff. 2015. "Recent development in hydrogen evolution reaction catalysts and their practical implementation." *Journal of Physical Chemistry Letters* **6**:951-957.
<http://dx.doi.org/10.1021/acs.jpcllett.5b00306>

Zhang, Xiuli, Yuan Cheng, Chunhu Li, Qingjie Guo, and Xiangchao Meng. 2020. "Catalytic hydrolysis of alkaline sodium borohydride solution for hydrogen evolution in a micro-scale fluidized bed reactor." *International Journal of Energy Research* **44**: 6758-6766.
<http://dx.doi.org/10.1002/er.5412>