



RESEARCH ARTICLE / ARAŞTIRMA MAKALESİ

Statistical Investigation of the Mineralogical Effect on Blastability in Granitic Rocks

Granitik Kayaçalarda Patlatılabilirlik Üzerindeki Mineralojik Etkinin İstatistiksel İncelenmesi

Orkun Kantarcı ^{1*}, Ayhan Kesimal ²

¹ Şırnak University, Faculty of Engineering, Department of Mining Engineering, Şırnak, TÜRKİYE

² Karadeniz Technical University, Faculty of Engineering, Department of Mining Engineering, Trabzon, TÜRKİYE

Corresponding Author / Sorumlu Yazar*: orkunkantarci@sirnak.edu.tr

Abstract

In this study, the effect of physico-mechanical and mineralogical properties of core samples taken from granite rocks obtained from different locations on blastability was statistically analyzed. The relationship between the mineral content of the rocks and rock mechanics parameters was evaluated. The best regression equations with strong relationships ($R^2 > 0.700$) involving the parameters used in the blastability formulas were then obtained. These equations were analyzed for five different blastability indices and the results of the forecasting accuracy analyses (RMSE= 0.000-0.085 and MAPE= 0.06-1.82) showed that the models were quite successful. According to the results of the best forecasting accuracy analysis, the parameters to be considered in the specific charge calculation were mineral content, uniaxial compressive strength, tensile strength, apparent porosity, density and ultrasonic P-wave velocity. As a result of the studies, it was concluded that the mineralogical composition of the rocks had a significant effect on the blastability parameters and lower specific charge values were achieved if the minerals are taken into account.

Keywords: Blastability, Rock Mechanics, Mineralogy, Statistics, MAPE, RMSE

Öz

Bu çalışmada farklı lokasyonlardan temin edilen granit kayaçlarından alınan karot numunelerinin fiziko-mekanik ve mineralojik özelliklerinin patlatılabilirliğe etkisi istatistiksel olarak incelenmiştir. Kayaçların mineral içeriklerinin ve kaya mekaniği parametrelerinin birbirleriyle olan ilişkisi değerlendirilmiştir. Sonrasında patlatılabilirlik formüllerinde kullanılan parametreleri içeren güçlü ilişkilere ($R^2 > 0,700$) sahip en iyi regresyon eşitlikleri elde edilmiştir. Bu eşitlikler beş farklı patlatılabilirlik indeksine göre incelenmiş ve yapılan tahmin doğruluğu analizlerinin sonuçları (RMSE= 0,000-0,085 ve MAPE= 0,06-1,82) modellerin oldukça başarılı olduğunu göstermiştir. En iyi uyum analiz sonuçlarına göre özgül şarj hesabında dikkate alınacak olan parametreler; Mineral içeriği, tek eksenli basınç dayanımı, çekme dayanımı, görünür porozite, yoğunluk ve ultrasonik P-dalga hızıdır. Çalışmalar sonucunda, kayaçların mineralojik bileşimlerinin patlatılabilirlik parametrelerine önemli etkisinin olduğu ve minerallerin dikkate alınması durumunda daha düşük özgül şarj değerlerine ulaşılmaktadır.

Anahtar Kelimeler: Patlatılabilirlik, Kaya Mekaniği, Mineraloji, İstatistik, MAPE, RMSE

1. Introduction

As a source of raw materials, mining has always been an essential engineering area for humanity. Blasting, which is used in the excavation process and where each step involves significant costs, has become a sensitive area in this sector. Recently, blasting has played an important part in both the mining and construction sectors, particularly with regard to tunneling and transport projects. The results of the blasting have a direct impact on all subsequent process.

In addition to the direct impact on the loading and transportation operations in mining, it also has a significant impact on the ore processing in terms of cost and efficiency through its size reduction. For this reason, the issue of blastability is of great importance in order to fully understand blasting, an important and attention-consuming application. Blastability indicates the sensitivity of the rock mass to explosions and is closely related to

the specific charge [1]. To date, numerous investigations into blastability have been carried out and these investigations used experimental blasting under field conditions.

According to Fraenkel [2], there was an empirical relationship between maximum burden, hole depth, charge diameter and charge height [3]. According to Hino [4], blastability coefficient was the ratio of compressive strength to tensile strength. Hansen [5] gave a formula for estimating the amount of explosives for the corresponding fragmentation required for the Marrow Point dam and power plant project. Sassa and Ito [6], in a study primarily concerned with tunneling applications, proposed the RBF (rock breakage field index) by conducting regression analyzes between crack frequency values and values from laboratory experiments on rock mechanics. Heinen and Dimock [7] defined blastability based on field studies in a copper mine in Nevada (USA) and showed a relationship between specific charge and seismic propagation [3]. Langefors [8] proposed a factor (rock constant)

that indicates the influence of rock. Praillet [9] defined the burden value as a function of bench height, charge density, detonation velocity, setting height, uniaxial compressive strength, and type of loading equipment [10]. Borquez [11] calculated the blastability factor (Kv) by correcting the drilling equation for the burden using RQD (Rock Quality Designation) with the alteration coefficient [1,10]. Ashby [12] empirically determined the specific charge required for blasting in the Bougainville copper mine (Papua New Guinea) based on the effective internal friction angle, which represent the strength of the rock mass and the crack frequency, which represent the crack density. Leighton et al. [13] developed an equation using the RQI (Rock Quality Index) value proposed by Mathis and a rotary drill [10,14]. Rakishev [15] defined blastability as the resistance to cracking by blasting. Lopez and Jimeno [16] proposed the drilling index for rock character, taking into account the limitations of the RQI [10]. The blasting index developed by Lilly [17] was derived from rock mass properties such as crack density and orientation, specific gravity and hardness. Ghose [18] suggested a geomechanical rock mass classification system and correlated specific charge with blastability under coal mine conditions [1,10]. Gupta et al. [19] attempted to estimate specific charge (kg/m³) values for different rock strengths based on field data [1,3]. JKMR [20] conducted blastability analysis of the coal layer and classified rock mass properties affecting blast performance [21].

Han et al. [22] used artificial neural networks (ANN) to define the blastability of a rock mass. They designed a back propagation network with 6 input, 5 hidden and 1 output processing elements. The concept of blastability was defined in the study by Rustan et al. [23] as the ability of rock to be fragmented by blasting. The most important physical and mechanical rock properties for blastability; Gokhale [3] explained the blastability index specified by the Norwegian University of Science and Technology (NTNU) about sample blastability in his book. Sawmliana and Pal Roy [24] suggested blastability for the French coal production technique of gallery fan-shaped blasting where roof management is difficult.

In the literature, the effect of mineralogy on the mechanical and physical properties of rocks examined [25], however no study on the mineralogical effect on blastability was found. Within the scope of this study, the parameters that may have an effect on blastability other than the parameters mentioned in the literature were tried to be statistically revealed as a result of petrographic analysis and rock mechanics experiments, and to express the extent of their effects through Mean Absolute Percentage Error (MAPE), Root Mean Square Error (RMSE) and R².

2. Materials and Methods

2.1. Material

Rock mechanics tests, mineralogical investigations and statistical studies were carried out on granite samples taken from five different regions in the Eastern Black Sea Region. The granite samples used in the study were obtained from Doğankent (Harşit) district of Giresun (1 piece), Of district of Trabzon (2 pieces) and İkizdere district of Rize (2 pieces). Mineralogical investigations of the samples were carried out at General Directorate of Mineral Research and Exploration (MTA, TÜRKİYE), and rock mechanics tests were carried out at Karadeniz Technical University, Department of Mining Engineering [26].

2.2. Methods

Core samples were prepared according to standards. Uniaxial compressive strength test (UCS), determination of elastic modulus (Young's modulus; E) and Poisson's ratio (ν), triaxial compressive strength test (TCS; c , ϕ), indirect tensile test (ITS; σ_t), density (ρ), unit volume weight (UVW), apparent porosity test (n) were performed according to ISRM [27] and ultrasonic P-wave velocity test (V_p) was performed according to ASTM-D2845 [28].

Based on the data obtained, a statistical analysis was carried out. In our study, the package program SPSS 17.0 was used to statistically evaluate the results. In rock engineering, researchers use multiple regression analyses to create a predictive model among relevant rock properties. Multiple regression analysis showed better predictive performance than simple regression analysis on rock mechanics properties.

After determining that the data were normally distributed, correlation analysis was performed to determine the degree of relationship between the variables. Upon identification of the correlated parameters, the relationship between these parameters was expressed mathematically using multiple regression analysis. In the analysis carried out using the ENTER method, the effects of the independent variables with correlation between them were observed. Therefore, the STEPWISE method was preferred in the multiple regression analysis. Whether the mathematical model formed as a result of the analysis is significant or not is determined by F and Sig. value in the output of the ANOVA analysis. As Sig. < 0.05, the model is significant. The aim of the stepwise method is to find a solution to the multicollinearity problem. The problem of multicollinearity is that the mathematical expression becomes meaningless due to the correlation between the independent variables that we add to increase the explanation rate of the dependent variable. Hence, selecting stepwise will determine the strongest model by eliminating the models that are correlated with each other. The relationship between the rock properties was determined by the Pearson correlation coefficient, and the degree of linear relationship between them was calculated by regression analysis.

Regression analysis provides an equation that mathematically expresses the degree of relationship between a dependent variable and one or more independent variables [29]. In regression analysis, the value of the coefficient of determination (R²) indicates the rate at which a change in the dependent variable is expressed by the independent variables added to the independent model [30]. In addition, the "F-statistic", which shows the significance of the mathematical models obtained as a result of regression analysis, and the "Sig. value" are important for the interpretation of regression models. If Sig. Value (p) < 0.05, it is concluded that this model is a significant model [31].

Beside the correlation coefficient, analysis of forecasting accuracy analyses (RMSE and MAPE) were calculated to verify the predicted performance of the models with the estimated and measured data, and the prediction performance both models were compared.

The percent prediction error (Eq. 1) was calculated to determine how close the prediction values were to the measured values. Although the values for MAPE (Eq. 2) and RMSE (Eq. 3) always take positive values, the ideal value is close to zero (Table 2.1.) [32].

$$\text{Prediction Error (\%)} = \frac{y - y'}{y} \cdot 100 \quad (1)$$

$$\text{MAPE (\%)} = \left[\frac{1}{N} \sum_{i=1}^N \frac{|y - y'|}{y} \right] \cdot 100 \quad (2)$$

$$RMSE (\%) = \sqrt{\frac{1}{N} \sum_{i=1}^N (y - y')^2} \tag{3}$$

y is the measured value and y' is the predicted values and N is the number of data.

Table 2.1. Classification of MAPE values [32,33]

MAPE (%)	Evaluation
MAPE ≤ %10	Very good prediction
% 10 < MAPE < % 20	Good prediction
% 20 < MAPE < % 50	Acceptable prediction
MAPE > % 50	False prediction

Data from rock mechanics experiments and petrographic studies of granites were applied to blastability formulas to calculate direct blastability values. The parameters that directly and indirectly affect the blastability were then tested by replacing the relevant parameters with mathematical models resulting from a regression analysis. The results were evaluated using the RMSE and MAPE values.

When determining the parameters used in the studies, a few principles were first established. These principles are: 1. When more than one parameter was present, only one parameter at a time and other parameters affecting it indirectly were applied in the regression analysis to understand their individual effects. 2. Average values representative of the granites were used for the analysis. 3. Since the formation of minerals was a natural process, they were taken into account directly in model identification and

were not considered dependent variables and were not replaced by any model.

According to the above principles, the relationships were studied, and the success of the models was demonstrated by analysis of forecasting accuracy between the directly obtained and the calculated results. The aim of the calculations carried out in this study was to demonstrate the need to investigate the parameters that influence blastability not only alone, but in a variety of ways. It was statistically proven that the neglected parameters also have an influence.

3. Results and Discussion

3.1. Physical and Mechanical Properties of Rocks

The mineralogical composition of Harşit (H), Hayrat Gray (HG), Hayrat Yellow (HS), İkizdere Yellow (İS) and İkizdere Blue (İM) samples were given in the table (Table 3.1). The results of the rock mechanical tests, which indicate the physical and mechanical properties of the rocks, were shown in Table 3.2. Of the rock mechanical data, only the parameters that influence blastability were analyzed in comparison to the literature.

Table 3.1 Mineralogical composition of Granitic rocks

Samples	Mineral Percentages (%)				
	İM	İS	HS	HG	H
Quartz	25	45	35	35	25
Alkali feldspar	30	35	40	40	30
Plagioclase	40	15	15	10	35
Mafic Minerals	4	4	5	5	8
Others	1	1	5	10	2

Table 3.2. Physical and mechanical properties of granites

Granite Group	ρ (g/cm ³)	UCS (MPa)	ITS (MPa)	Vp (km/sn)	n (%)	c (MPa)	φ (o)	E (GPa)	v
İM	2.639	181.28	12.50	4.682	0.60	17.84	63	67.05	0.21
İS	2.613	112.39	11.46	3.658	0.85	13.55	60	47.21	0.25
HS	2.619	148.39	10.83	4.131	0.98	19.81	57	45.97	0.25
HG	2.621	153.23	10.78	4.243	0.86	19.56	59	60.03	0.22
H	2.699	206.89	14.66	4.695	0.56	23.72	60	69.14	0.20

ρ: Density, UCS: Uniaxial Compressive Strength, ITS: Indirect Tensile Strength, Vp: Ultrasonic P-Wave Velocity, n: Apparent Porosity, c: Cohesion, φ: Internal Friction Angle, E: Modulus of Elasticity, v: Poisson's Ratio

3.2. Statistical Analysis

3.2.1. Simple and multiple regression tests

In studies on blastability, the most effective parameters from the physical and mechanical properties of rocks were density (ρ), modulus of elasticity (E), ultrasonic P-wave velocity (Vp),

uniaxial compressive strength (UCS), indirect tensile strength (ITS), internal friction angle (φ) values. In the statistical analysis tests, simple and multiple regression tests were performed and only the models with R² values above 0.700 (Table 3.3.) within the significant values of the resulting data were used in the explosibility calculation.

Table 3.3. Statistical analysis of dependent variables affecting blastability

Dependent Variable	Equation No	Regression	Compliance Test	Anova Test	
ρ	D1	$\rho = 2.634 + 0.015 * Maf - 0.093 * n$	R ² = 0.889	F: 87.982	Sig.: 0.000
E	D2	$E = 35.665 + 15.675 * Vp - 197.636 * v$	R ² = 0.758	F: 34.434	Sig.: 0.000
	D3	$E = -58.546 + 31.119 * Vp - 215.472 * v + 0.974 * K$	R ² = 0.807	F: 29.360	Sig.: 0.000
Vp	D4	$Vp = 2.385 + 0.012 * UCS$	R ² = 0.902	F: 212.166	Sig.: 0.000
	D5	$Vp = 5.977 - 0.051 * K$	R ² = 0.853	F: 133.200	Sig.: 0.000
	D6	$Vp = 2,421 + 0.014 * UCS - 0.087 * Maf$	R ² = 0.953	F: 222.198	Sig.: 0.000
UCS	D7	$UCS = -166.242 + 76.295 * Vp$	R ² = 0.902	F: 212.166	Sig.: 0.000
	D8	$UCS = 296.391 - 4.120 * K$	R ² = 0.851	F: 130.897	Sig.: 0.000
	D9	$UCS = -152.806 + 65.151 * Vp + 6.592 * Maf$	R ² = 0.967	F: 321.773	Sig.: 0.000
	D10	$UCS = -533.214 + 61.533 * Vp + 4.098 * Maf + 154.981 * \rho$	R ² = 0.973	F: 250.992	Sig.: 0.000
ITS	D11	$ITS = -54.472 + 27.127 * \rho - 0.144 * AF$	R ² = 0.784	F: 39.863	Sig.: 0.000
	φ	D12	$\phi = 77.643 - 0.414 * AF - 0.643 * Maf$	R ² = 0.867	F: 71.720
φ	D13	$\phi = 73.728 - 0.359 * AF - 0.730 * Maf + 0.042 * E$	R ² = 0.915	F: 75.043	Sig.: 0.000
	D14	$\phi = 73.453 - 0.243 * AF - 0.799 * Maf + 0.035 * E - 3.937 * n$	R ² = 0.942	F: 81.840	Sig.: 0.000

3.2.2. Blastability Analysis

3.2.2.1. Blastability According to Hino

In the study by Hino [4], compressive and tensile strengths were used as rock mechanical parameters. The aim here was to demonstrate how close the coefficient value calculated with the values of the existing parameters taking into account the equation from Hino [4] was and the coefficient value calculated with the parameters determined from the regression model. For this reason, in this study, the direct effect of the strength

parameters on the blastability was evaluated by replacing the strength parameters and then the indirect effect parameters were evaluated using high R² regression models expressing the compressive strength (Table 3.4). The parameters, that directly affect the Hino [4] equation, were UCS and ITS. According to the forecasting accuracy analysis, the best results were obtained with equations D10 and D9 (ITS constant) and D11 (UCS constant), respectively. Consequently, V_p, mafic mineral content and density were the primary parameters, beside quartz content and alkali feldspar content also influence the blastability.

Table 3.4. Direct and indirect calculation of blastability with rock mechanics parameters according to Hino [4].

Blastability Formula	Direct Account		Indirect Account				
	Equation	Sample name	ITS (constant)			UCS (constant)	
			D8	D7	D9	D10	D11
$\text{Blastability coefficient} = \frac{UCS}{ITS}$	IM	14.502	15.471	15.278	14.288	14.422	14.163
	IS	9.807	9.685	9.847	9.763	9.88	9.885
	HS	13.702	14.053	13.752	13.785	13.607	13.727
	HG	14.214	14.118	14.609	14.526	14.339	14.097
	H	14.113	13.192	13.094	14.039	14.104	14.347
	RMSE		0.622	0.6	0.177	0.085	0.195
MAPE		3.54	3.22	1.04	0.58	1.16	

3.2.2.2. Blastability According to Ashby

The Ashby [12] equation differs from the Hino [4] equation in that it calculates the specific charge directly. Considering the blastability equation presented in his study, he used density, internal friction angle, and crack frequency. In this equation, Ashby [12] attempted to explain blastability by considering the intrinsic parameters between discontinuities and grains. Density and angle of internal friction were parameters that are directly substituted and the other parts were assumed to be constant

(Table 3.5). The roughness angle was considered within the internal friction angle, while the crack frequency was taken to be 10, which corresponds to the bedrock transition zone reported in his study. By direct calculation, it was calculated that the blastability of the granites in the study varies between 1.0 and 1.3 kg/m³. When evaluated with regression models, the calculated specific charge was between 1.0 and 1.3 kg/m³, as in the direct calculation, and was above the specific charge value given by Dyno Nobel (0.7 to 0.8 kg/m³) [34].

Table 3.5. Direct and indirect calculation of blastability with rock mechanics parameters according to Ashby [12].

Blastability Formula	Direct Account		Indirect Account			
	Equation	Sample name	Internal Friction Angle (constant)		Density (kg/m ³) (constant)	
			D1	D12	D13	D14
$\text{Specific Charge} = \frac{0.56 \cdot \rho \cdot \tan(\phi + i)}{\text{crack/meter}}$	IM	1.347	1.346	1.326	1.338	1.344
	IS	1.177	1.178	1.205	1.188	1.179
	HS	1.049	1.048	1.084	1.075	1.068
	HG	1.134	1.137	1.085	1.101	1.110
	H	1.215	1.217	1.219	1.216	1.215
	RMSE		0.000	0.032	0.020	0.014
MAPE		0.14	2.38	1.42	0.86	

As can be seen from the values in Table 3.5, the RMSE and MAPE values obtained when the regression models were substituted for the density and internal friction angle values used in Ashby's [12] study were close to perfect. Furthermore, ρ and φ directly affected the angle, while Maf, n, AF and E indirectly affected the blastability. Alkaline Feldspar content, Mafic Mineral content, Modulus of Elasticity and Apparent Porosity values had a strong effect on blastability when MAPE and RMSE values in multiple regression were analyzed. This was seen in the analysis calculated according to equations D1, D14 and D13.

3.2.2.3. Blastability According to Rakishev

Rakishev's [15] examined the influence of the mechanical properties of many rocks on blastability and attempted to calculate a critical velocity required for cracking. He tried to explain the blastability of the rock based on the calculated speed.

Rakishev [15] used compressive strength, tensile strength, density and ultrasonic P-wave velocity in his formula. In the study conducted by Rakishev [15], the average k was 0.964, the g was 9.807 m/s² and the average dn was 0.51 m, which were found from the values given for granodiorite rocks. RMSE and MAPE values were calculated between the predicted and actual values

and RMSE and MAPE, the best value, were performed (Table 3.6a,b).

Table 3.6a. Direct and indirect calculation of blastability with rock mechanics parameters according to Rakishev [15].

Blastability Formula	Equation	Direct Account (km/s)	Indirect Account (km/s)				
			UCS, Vp, ITS (constant)		ρ, Vp, ITS(constant)		
			Density	UCS			
		D1	D8	D7	D9	D10	
$\text{Critical Crack Velocity} = \frac{k \sqrt{g \cdot d_n + \frac{0.1 \cdot UCS + ITS}{\rho \cdot V_p}}}{\rho \cdot V_p}$	Sample name						
	IM	4.635	4.636	4.733	4.713	4.613	4.627
	IS	4.531	4.529	4.516	4.536	4.525	4.540
	HS	4.529	4.530	4.564	4.534	4.537	4.519
	HG	4.503	4.496	4.494	4.541	4.533	4.515
	H	4.946	4.943	4.839	4.828	4.937	4.945
	RMSE		0.000		0.068	0.066	0.020
MAPE		0.06		1.12	1.02	0.32	0.18

Table 3.6b. Direct and indirect calculation of blastability with rock mechanics parameters according to Rakishev [15].

Blastability Formula	Equation	Direct Account (km/s)	Indirect Account (km/s)			
			UCS, ITS, ρ (constant)			ρ, Vp, UCS (constant)
			Vp	ITS		
		D5	D4	D6	D11	
$\text{Critical Crack Velocity} = \frac{k \sqrt{g \cdot d_n + \frac{0.1 \cdot UCS + ITS}{\rho \cdot V_p}}}{\rho \cdot V_p}$	Sample name					
	IM	4.635	4.624	4.701	4.673	4.659
	IS	4.531	4.515	4.483	4.539	4.521
	HS	4.529	4.494	4.509	4.570	4.527
	HG	4.503	4.531	4.513	4.567	4.511
	H	4.946	4.943	4.845	4.991	4.927
	RMSE		0.020	0.058	0.042	
MAPE		0.40	1.04	0.84		0.26

When calculated directly, the resulting velocity values were between 4.5-4.9 km/s. These results were consistent with the values given by Rakishev [15] for igneous rocks in his study in the range of 3.65-4.88 km/s. When analyzing Table 3.6b, it becomes clear that the indirect calculation based on density produces almost perfect results. In the same way, another good result was obtained from the indirect calculation according to equation D10 (MAPE: 0.18, RMSE: 0.000) for ITS and UCS. According to Rakishev [15], the granites used in the study were considered difficult to blast (Table 3.7).

Table 3.7. Correlation between critical crack velocity and blastability [15]

Critical crack velocity (m/s)	Blastability
3,6 > V _{cr}	Easy to blast
3,6 < V _{cr} < 4,5	Partially easy to blast
4,5 < V _{cr} < 5,4	Difficult to blast
5,4 < V _{cr} < 6,3	Very difficult to blast
6,3 < V _{cr}	Extremely difficult to blast

When Table 3.6 was examined; It was statistically shown that in addition to the directly influencing parameters (density, ITS, UCS and Vp), the quartz content, the mafic mineral content, the alkali feldspar and the apparent porosity also had an influence on the blastability. Taking MAPE and RMSE into account, the results were at a very good level of prediction. The best results were obtained with equations D1, D10 and D11, respectively.

3.2.2.4. Blastability According to Lilly

Lilly [17] proposed a method that is easier to use. According to this method, the condition of the joints (openness and alignment)

was important. The calculated index value was then designated from Figure 3.1 which the number in relation to the specific charge and the required amount of ANFO was determined. In the study by Lilly [17], the rock mechanical parameters that contribute to the equation include; Given the values considered in this study, only the density parameter was used. The blast index developed by Lilly [17] was derived from rock mass properties such as crack density and orientation, specific gravity and hardness. The constant values were taken from his table (RMD:50, JPS:10, JPO:30, H:7) (Table 3.8.). The results of the density substituted regression model are shown in the following table (Table 3.9).

Table 3.8. Blastability index parameters according to Lilly [17].

(Rock mass definition)	RMD	Crumbly/Fragmentable rock mass	10
		Blocky rock mass	20
		Completely massive rock mass	50
(Distance between planes)	JPS	Close range (<0.1m)	10
		Moderate (0.1-1.0 m)	20
		Wide range (>1.0 m)	30
(Joint plane orientation)	JPO	Horizontal	10
		Branching out of the slope	20
		Normal sheet orientation with slope	30
		Inwardly branched from the slope	40

By analyzing the results in Table 3.9, it was found that the density in indirect calculation had excellent MAPE and RMSE values. It was also found that mafic mineral content and apparent porosity could be used as parameters instead of density. Therefore, taking into account the study of Lilly [17], it was statistically proven that mafic mineral content and apparent porosity had an influence on blastability.

Table 3.9. Direct and indirect calculation of blastability with rock mechanics parameters according to Lilly [17].

Blastability Formula	Direct Account		Indirect Account	
	Equation		ρ	D1
	Sample name			
$\text{Blasting index} = 0.5 \left(\frac{RMD + JPS}{SGI + M} \right)$	IM	56.488		56.475
	IS	56.163		56.188
	HS	56.238		56.225
	HG	56.263		56.363
	H	57.238		57.275
	RMSE			0.049
	MAPE			0.06

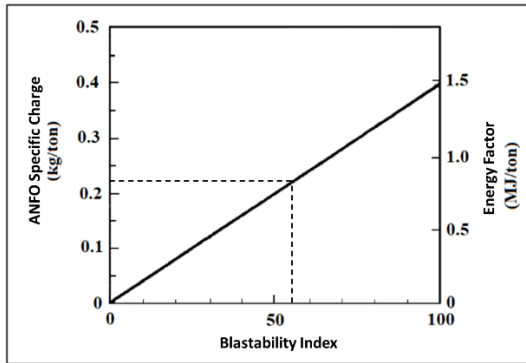


Figure 3.1. Blastability index-specific charge relationship [17].

Considering Figure 3.1, the calculated values for the rocks used in this study varied by approximately 0.23 kg/ton (0.62 kg/m³) and the specific charge values were below and close to the specific charge value (0.7– 0.8 kg/m³) given by Dyno Nobel [34]. According to the result of the MAPE and RMSE analysis, the process had very good predictive values based on the only available variables (Eq. D1).

3.2.2.5. Blastability According to Gupta

In the study conducted by Gupta [19], the parameters specified in the blastability formula included UCS and modulus of elasticity, which are the rock mechanics parameters used in this study, and the rest were considered constant, and the results were given in Table 3.10. The constant burden in Gupta's equation was accepted as 1.2 m considering the field applications [19]. Table 3.10 showed that the best results were obtained with equations D9 and D10 based on UCS. Gupta [19] directly calculates the specific charge (kg/m³) and this value varied between 0.49-0.82 kg/m³ for the rocks studied. As can be seen from the figure below; in Gupta's [19] research, it was statistically revealed that Vp, density and mafic mineral content, quartz content and Poisson's ratio also affect the specific charge. In the calculations made with the models, the specific charge value varies between 0.49-0.84 kg/m³ and was in accordance with the specific charge (0.7-0.8 kg/m³) value range specified by Dyno Nobel [34]. According to the prediction accuracy analysis, the best results are obtained with equations D9, D10 and D3, respectively.

Table 3.10. Direct and indirect calculation of blastability with rock mechanics parameters according to Gupta [19].

Blastability Formula	Equation	Direct Account (kg/m ³)	Indirect Account (kg/m ³)						
			UCS (constant)			E (constant)			
			E	D2	D3	D8	D7	D9	D10
	Sample name								
$\text{Specific Charge} = 0.278 B^{-0.407} F^{0.6}$	IM	0.722	0.722	0.731	0.786	0.774	0.712	0.720	
	IS	0.490	0.524	0.512	0.491	0.501	0.496	0.503	
	HS	0.722	0.670	0.677	0.738	0.718	0.720	0.709	
	HG	0.619	0.640	0.630	0.625	0.652	0.648	0.637	
	H	0.826	0.834	0.841	0.771	0.764	0.833	0.838	
	RMSE		0.028	0.024	0.037	0.040	0.014	0.014	
	MAPE		3.70	3.12	3.78	4.56	1.68	1.82	

4. Conclusions

Within the scope of this study, rock mechanics experiments, mineralogical investigation and statistical studies were carried out on granite samples taken from five different regions in the Eastern Black Sea Region ("H" Harşit region, "HG and HS" Of region and "IM and IS" İkizdere region). The findings obtained as a result of the studies were given below.

- As a result of the study, a strong correlation was found between blastability and mineral distribution.
- Considering the study of Hino [4], the best result was obtained from equation D10. The analysis of forecasting accuracy (MAPE

and RMSE) results of this equation containing Vp - Mafic Mineral - ρ were 0.085 of RMSE and 0.58 of MAPE.

- Considering the Ashby [12] study, the best analysis of forecasting accuracy result was obtained with regression equation D14 containing Alkali Feldspar - Mafic Mineral - E - n (RMSE: 0,014, MAPE: 0,86).
- Considering the formula of Rakishev [15], the best result was obtained with equation D1 containing Mafic Mineral-n, where UCS, ITS, Vp were constant (RMSE: 0,000 MAPE: 0,06).
- When the study of Lilly [17] was analyzed, the model was in a very good prediction range. While other parameters were

constant, the best analysis of forecasting accuracy were obtained with equation D1 (Mafic Mineral-n) (RMSE: 0.014, MAPE: 0.26).

- Gupta [19] concluded that when E was constant, the model with equation D9 with Mafic Mineral - n was the best analysis of forecasting accuracy (RMSE 0.014, MAPE 1.82).

As a result of the evaluations made by statistical analysis, it was revealed that mineralogy had an effect on the parameters used in the calculation of blastability and the specific charge value decreased even more when minerals were taken into account. The values given were all in terms of specific charge except Hino [4] and Rakishev [15]. When the calculated values were examined, the parameters to be taken into account in the specific charge calculation according to the best analysis of forecasting accuracy results were mineral content, uniaxial compressive strength, indirect tensile strength, apparent porosity, density and ultrasonic P-wave velocity. In future studies, it is recommended to create a new blastability index including the mineral structure and the mentioned parameters with detailed field and laboratory model blasting studies.

Ethics committee approval and conflict of interest statement

There is no need to obtain permission from the Ethics Committee or the article prepared.

There are no conflicts of interest with any individual or institution in this article.

Acknowledgment

This article has been produced from PhD thesis named "Investigation of the effect of physico-mechanical and mineralogical properties on the blastability of granitic rocks".

References

- [1] Dey, K. ve Sen, P., 2003. Concept of Blastability – An Update. *The Indian Mining and Engineering Journal*, 42, 8-9, 24 – 31.
- [2] Fraenkel, K.H., 1954. *Handbook in rock blasting technique*, Part-1, Esselte AB, Stockholm.
- [3] Gokhale, B.V., 2011. *Rotary Drilling and Blasting in Large Surface Mines*, CRC Press London.
- [4] Hino, K., 1959. *Theory and Practice of Blasting*, Nippon Kayaku Co. Ltd., Asa, Yamaguchi-Ken, Japan
- [5] Hansen, D. W., 1967. *Drilling And Blasting Techniques For Morrow Point Power Plant*. The 9th U.S. Symposium on Rock Mechanics (USRMS), 17-19 April, Golden, Colorado.
- [6] Sassa K. ve Ito I., 1974. On the relation between the strength of a rock and the pattern of breakage by blasting, *Proc. 3rd Int. Congress Rock Mechanics Denver, II-B*, 1501-1505.
- [7] Heinen R. H. ve Dimock R.R., 1976. The Use of Sonic Measurements to Determine The Blastability of Rocks, *Proceedings Second Conference on Explosive and Blasting Techniques*, Louisville, Kentucky, 234-248.
- [8] Langefors, U., 1978. *The Modern Technology of Rock Blasting*, John Wiley & Sons Inc, New York, 438.
- [9] Praillet, R., 1980. A new approach to blasting.
- [10] Jimeno C.L., Jimeno, E.L. ve Carcendo, F.J.A., 1995. *Drilling and Blasting of Rocks*, AA-Balkema, Rotterdam, Brookfield.
- [11] Borquez, G.V., 1981. Estimating Drilling and Blasting Costs and Analysis and Prediction Model. *EEMJ*. January, 83-89.
- [12] Ashby, J.P., 1981. Production blasting and the development of pit slopes, *Proceeding of the 3rd. International Conference on stability in open pit mining*, Vancouver, B.C
- [13] Leighton, J.C., Brawner, C.O. ve Stewart, D., 1982. Development of a correlation between rotary drill performance and controlled blasting powder factors, *Can. Inst. Min. Bull.*, 844, 67-73.
- [14] Mathis, C., 1975. Proposal of a report on Rock Quality Index based on rotary drill Performances, Unpublished paper, University of Alberta, March.
- [15] Rakishev, B.R., 1982. A New Characteristics of the Blastability of Rock in Quarries, *Soviet Mining Science*, 17, 248-251.
- [16] Lopez Jimeno, E. ve Lopez Jimeno, C., 1984. Las Voladuras en Crater y su Aplicacion ala Minería, VII Congress International de Minería y Metalurgia, Barcelona
- [17] Lilly P., 1986. An Empirical Method pf Assessing Rockmass blastability, *Large Open Pit Mine Conference*, Newman, Australia, 89-92.
- [18] Ghose A.K., 1988. Design of drilling and blasting subsystems – A rockmass classification approach, *Mine Planning and Equipment Selection*, Balkema.
- [19] Gupta, V. ve Sharma, R., 2012. Relationship between textural, petrophysical and mechanical properties of quartzites: A case study from northwestern Himalaya, *Engineering Geology*, 135-136, 1–9.
- [20] JKMR, 1996. *Open pit blast design analysis and optimisation*, Julius Krutchnitt Mineral Research Centre, Indooroopilly, Australia, 338.
- [21] Pal Roy, P., 2005. *Rock blasting effects and operations*, Rotterdam: Balkema, 223–240.
- [22] Han, J., Weiya, X. ve Shouyi, X., 2000. Artificial neural network method of rock mass blastability classification. *Proceedings of the Fifth International Conference on Geo Computation*, London, UK, 23–25.
- [23] Rustan, A., Cunningham, C., Fourney, W., Spathis, A. ve Simha, K.R.Y., 2010. *Mining and Rock Construction Technology Desk Reference: Rock Mechanics, Drilling & Blasting*, Technology & Engineering, 466.
- [24] Sawmliana, C. ve Pal Roy, P., 2012. A New Blastability Index for Hard Roof Management in Blasting Gallery Method, *Geotechnical and Geological Engineering*, 30, 6, 1357–1367.
- [25] Ersoy, H. ve Acar, S., 2016. Influences of petrographic and textural properties on the strength of very strong granitic rocks, *Environ Earth Sci*, 75,1461.
- [26] Kantarcı, O. 2017. Investigation of the effect of physico-mechanical and mineralogical properties on the blastability of granitic rocks. PhD Thesis, Technical University, Graduate School of Natural and Applied Sciences, Trabzon (in Turkish).
- [27] ISRM., 2007. The complete ISRM suggested methods for rock characterization, testing and monitoring: 1974–2006. In: Ulusay, Hudson (Eds.), *Suggested methods prepared by the commission on testing methods*, International Society for Rock Mechanics. ISRM Turkish National Group, Ankara, Turkey, 628.
- [28] ASTM D2845, 1983. *Standard Test Method for Laboratory Determination of Pulse Velocities and Ultrasonic Elastic Constants of Rock*.
- [29] Bayazıt, M. and Yeğen Oğuz, E.B., 2005. *Statistics for Engineers*, Birsen Publishing House, Istanbul, 197p.
- [30] Kılıç, E., 2007 *Statistical analysis of consolidation parameters*, Master Thesis, İstanbul Technical University, Institute of Science, İstanbul.
- [31] Dursun, A.E., 2012. *Cutability of Limestones Located in the Northwest of Konya City Center*, T.C. Selçuk University, Institute of Science, Konya
- [32] Karaman, K., Kaya, A. ve Kesimal, A., 2015. Effect of the specimen length on ultrasonic P-wave velocity in some volcanic rocks and limestones, *A Journal of African Earth Sciences*, 112, 142-149.
- [33] Lewis, C.D., 1982. *International and Business Forecasting Methods*. Butterworths, London.
- [34] Dyno Nobel, 2010. *Blasting and Explosives Quick Reference Guide*.